

Est.  
1841

YORK  
ST JOHN  
UNIVERSITY

Gupta, Abhishek, Kowalczyk, Marek, Heaselgrave, Wayne, Britland, Stephen T., Martin, Claire and Radecka, Iza (2019) The production and application of hydrogels for wound management: A review. *European Polymer Journal*, 111. pp. 134-151.

Downloaded from: <https://ray.yorks.ac.uk/id/eprint/3649/>

The version presented here may differ from the published version or version of record. If you intend to cite from the work you are advised to consult the publisher's version:  
<https://www.sciencedirect.com/science/article/pii/S0014305718318317>

Research at York St John (RaY) is an institutional repository. It supports the principles of open access by making the research outputs of the University available in digital form. Copyright of the items stored in RaY reside with the authors and/or other copyright owners. Users may access full text items free of charge, and may download a copy for private study or non-commercial research. For further reuse terms, see licence terms governing individual outputs. [Institutional Repositories Policy Statement](#)

# RaY

Research at the University of York St John

For more information please contact RaY at  
[ray@yorks.ac.uk](mailto:ray@yorks.ac.uk)

**Title: Production and Application of hydrogels in Wound Management: A Review**

**Authors:** Abhishek **Gupta**<sup>1&5</sup>, Marek **Kowalczuk**<sup>2&6</sup>, Wayne **Heaselgrave**<sup>2&5</sup>, Stephen T. **Britland**<sup>3</sup>, Claire **Martin**<sup>4</sup> and Iza **Radecka**<sup>2&5</sup>

<sup>1</sup>School of Pharmacy, <sup>2</sup>Wolverhampton School of Sciences, <sup>3</sup>School of Health Sciences, York St John University, York, UK, <sup>4</sup>Department of Biological Sciences, Institute of Science and the Environment, University of Worcester, U.K, <sup>5</sup>Research Institute in Healthcare Science, Faculty of Science and Engineering, University of Wolverhampton, Wulfruna Street, Wolverhampton, WV1 1LY, U.K, <sup>6</sup>Centre of Polymer and carbon Materials, Polish Academy of Sciences, Zabrze, Poland.

**Corresponding author:**

[Abhishek Gupta and Iza Radecka](#)  
Faculty of Science and Engineering  
University of Wolverhampton  
Wulfruna Street  
Wolverhampton  
WV1 1LY  
United Kingdom

Email: [a.gupta@wlv.ac.uk](mailto:a.gupta@wlv.ac.uk); [I.Radecka@wlv.ac.uk](mailto:I.Radecka@wlv.ac.uk)

Tel.: +44 [0] 1902-322673; 01902-322366

NOTE: The name and address of the author to whom requests for reprints should be addressed is the same as the corresponding author.

### Highlights:


- Advanced wound dressings account for over 60% of sales in a market worth \$11.4 billion annually
- Increased cases of diabetes worldwide and diabetic ulcers is key driving factor for the growth of this industry
- Hydrogels are an innovative type of dressing which uses moisture to aid the healing process
- Our focus is preparation methods, wound products and material aspect of hydrogel dressings.

**Comment [GA1]:** As per the journal guidelines, kindly make each point to maximum 85 characters

## **Abstract**

Wound treatment has gained huge impact in the wound care sector due to the pervasiveness of chronic wounds in the high risk population including, but not limited to, geriatric population, immunocompromised and obese patients. Rising prevalence of diabetes is another leading factor of the growth in chronic wound. According to the World Health Organization (WHO), the global diabetic prevalence has increased from 4.7% in 1980 to 8.5% in 2014. Moreover, according to the National Institute for Health and Care Excellence (NICE), in 2016, the prevalence of chronic venous leg ulcers alone was around 0.1% to 0.3% in the U.K. Wound dressings play an imperative role in wound healing process as they protect the wound site from external environment and are capable of interacting with the wound bed to facilitate and accelerate healing. Hence, the demand for advanced wound dressing products is rising. Advanced wound care that hydrogel wound dressings form part of, make up around \$7.1 billion of the market and they are growing at an annual rate of 8.3% with the market projected to be worth \$12.5 billion by 2022. Hydrogels, due to high water content, are ideal candidates for wound management as advanced moist dressings for wound healing. These wound dressing materials can be used for both: exudating or dry necrotic wounds. Additionally, hydrogels demonstrate other important features such as softness, malleability and biocompatibility. Presented review focuses on hydrogel wound dressings, their main characteristics and their wound management applications. It also describes recent technologies used for their production and the future potential developments.

### Graphical abstract

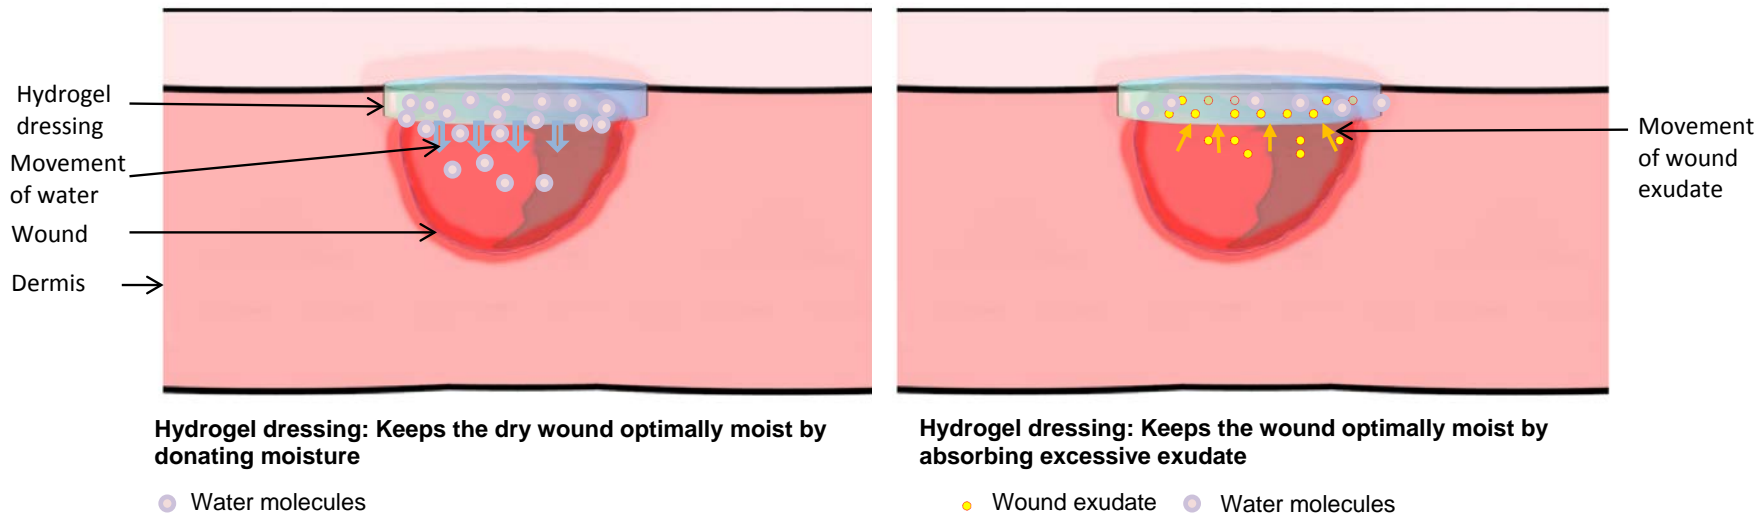

**Keywords:** Hydrogels; Chronic wounds; Wound healing; Wound management; Moist wound dressings

## **1. Introduction**

A wound is an injury that disrupts the integrity of the epidermis as a physical barrier thereby interrupting its normal anatomical structure and physiology [1]. Dermal injury can be caused by acute trauma or surgical event. The resultant damage can affect local epidermal tissue, the vascular network and depending on the nature and depth of the wound, dermal intricate structure may also get damaged. In the case of surgical incisions, as the tissue loss is minimal and the healing process is rapid, wounds can be closed by variety of techniques including adhesive strips, sutures or skin adhesives (closure by primary intention) unless there is any underlying pathological condition hindering the healing process. In the case of acute trauma associated with substantial dermal matrix loss, closure by secondary intention, allowing the defect to be filled with granulation tissue is the primary approach followed for repair process. Reparative process is protracted when the defect area is large due to increased demand for production of dermal matrix forming cells for healing [2].

Wound healing is a complex biological process that varies in completeness and length of time to resolution depending on whether the wound is acute or chronic [3]. Acute wounds follow the normal healing path and are generally resolved within 8-12 weeks; however chronic wounds like diabetic foot ulcers, pressure ulcers, venous leg ulcers, are difficult to heal and generally exceed 12 weeks to full resolution [4,5].

### **1.1. The Wound Healing Process**

Wound healing is a continuous process that follows a complex series of cellular and biochemical cascades occurring in orderly, sequential but overlapping phases to repair and regenerate the damaged tissue [6]. The healing process occurs in the

following four stages (Figure 1): exudative, inflammatory, proliferative and regenerative [7]. Various growth factors, cytokines, chemokines and other biomolecules are involved in this process [7,8,9] and their role in wound healing are summarised in Table 1. The exudative stage, also called coagulation and haemostasis, consists of stopping blood loss and preventing excessive bleeding. Although the act of bleeding is beneficial; washing the damaged tissue and reducing microbial invasion, it is controlled by haemostatic reflex vasoconstriction (local and systemic) and by the formation of insoluble fibrin plug, to prevent excessive blood loss. As blood interacts with exposed collagen and other components of the extracellular matrix, activated platelets release clotting factors and aggregate into a plug-like matrix, thus controlling blood loss [10]. Once haemostasis has been achieved, the inflammatory (or resorptive) stage begins with an increased infiltration of phagocytes (neutrophils and macrophages). The presence of neutrophils is time restricted to the early stages of healing, whereas macrophages persist through all phases from exudative to regenerative [11]. Within 24-36 hours post-injury, neutrophils migrate into the wound site and initiate phagocytic activity of macrophages by releasing proteolytic enzymes, chromatin, protease 'traps' and free-radical reactive oxygen species (ROS), with concurrent localised inflammation, heat and redness. The combined activity of neutrophils and macrophages helps to clear damaged and/or necrotic tissues, particulate contaminants and microorganisms from the wound site [12,13,14]. To enable the healing process to progress, neutrophils are removed from the wound site by apoptosis, phagocytosis (by macrophages), and disposal from the surface by sloughing or autolytic debridement. Modified monocyte macrophages arrive at the wound site 48-72 hours post-injury and phenotypically change into reparative tissue macrophages [11,15,16] that both promote and resolve

inflammation as well as removing apoptotic cells (by phagocytosis) [13,14]. Macrophages stimulate angiogenesis and granulation tissue formation in the later stages [17]. Infected wounds typically become halted in the inflammatory stage and hence fail to follow the normal healing process [18]. Wound debridement, which involves the removal of non-viable, hyperkeratotic tissue and microorganisms, is a vital stage of the healing process; chronic wounds can develop from a combination of poor debridement and microbial invasion, that both delay proliferation and tissue regeneration [19].

Once autolytic debridement is successfully achieved and the immune response has resolved, wound healing progresses into the proliferation stage which is the phase of tissue formation. During this stage tissue repair starts and wound closure is initiated. The wound site is filled with granulation tissue and epithelialisation from the wound edges takes place. The epithelial cells around the wound edges divide mitotically and migrate until a continuous sheet of cells is formed. Collagen (type III) formation by fibroblasts acts as a provisional matrix and provides strength to the newly formed granulation tissue which is responsible for scar formation [6,20]. To ensure the supply of oxygen and nutrients to newly formed tissue, angiogenesis also occurs at this stage with a microvascular network of new blood capillaries forming from the surrounding viable blood vessels [14,21]. The final stage of wound healing is regeneration where normal dermal architecture is restored and scar tissue tensile strength increased. Inflammatory cells clear from the regenerated area whilst collagen undergoes remodelling to increase the tensile strength of the tissue [6].

Healthy wound healing follows these sequential stages but delayed healing can result from several factors, including, but not limited to, underlying long term disease states such as diabetes, an impaired (HIV) or altered immune response (patients


undergoing immunosuppression therapy) and/or a high level of microbial burden on and around the wound [22,23].

A retrospective cohort analysis revealed that during 2012/2013, the total annual health economic burden spent by the National Health Service (NHS) in the UK on wound management was nearly £5.3 billion which equated to approximately 4% of the annual public health expenditure in the UK in 2013 (£125.5 billion), spent on wound management alone. During this year, wound care was provided to estimated 2.2 million patients and the outcome of the treatment revealed that only 61% wounds healed whereas 39% of wounds didn't heal during the duration of the study. Since many chronic non-healing wounds do not respond to the standard care, the cost of management for these wounds was substantially greater (£3.2 billion) than acute wounds (2.1 billion) [24]. While chronic non-healing wounds occur in all age groups but these are prevalent in elderly population. Moreover, obese community and diabetic patients are more at risk. Globally, the population is aging rapidly; obesity and diabetic cases are also increasing, which is leading to the staggering increase of number of chronic wound. Studies suggested an estimated annual increase of 6-7% in the number of venous and pressure ulcers and around 9% increase in cases of diabetic ulcers, which would put extra financial strain on health services [25].


Despite the emergence of new therapies and vast variety of dressings, there is still an urgent need for effective approach to tackle this growing challenge and hydrogels are a vital candidate as an advanced wound dressing to encounter this problem.

**Figure 1.** Illustration of the stages of wound healing, (a) Exudative stage with the formation of blood clot (b) Inflammatory stage, marked with oedema, pain and inflammation (c) Proliferation stage with granulation tissue formation and (d) Regenerative stage, characterised by scar tissue formation.


**(a) Exudative stage**

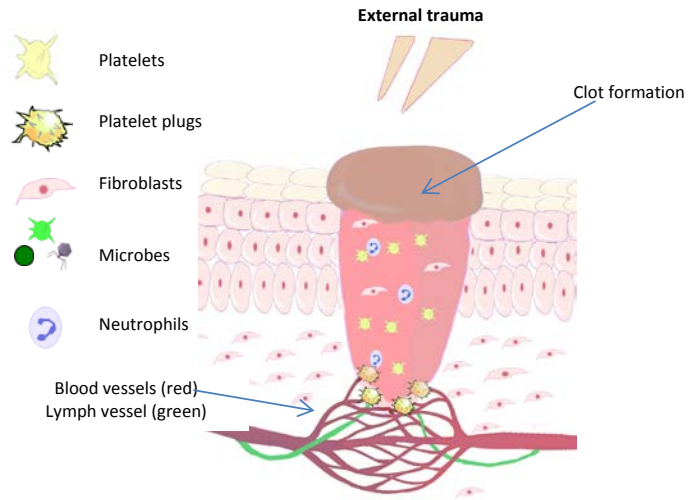


**(b) Inflammatory stage**

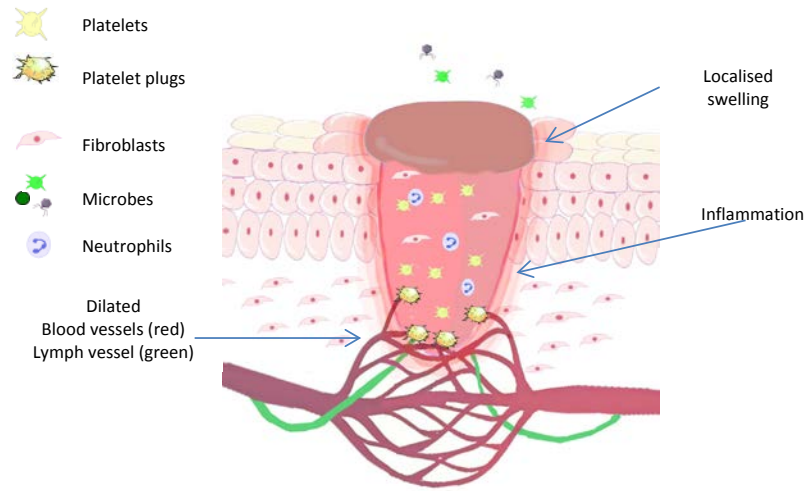

**(c) Proliferative stage**

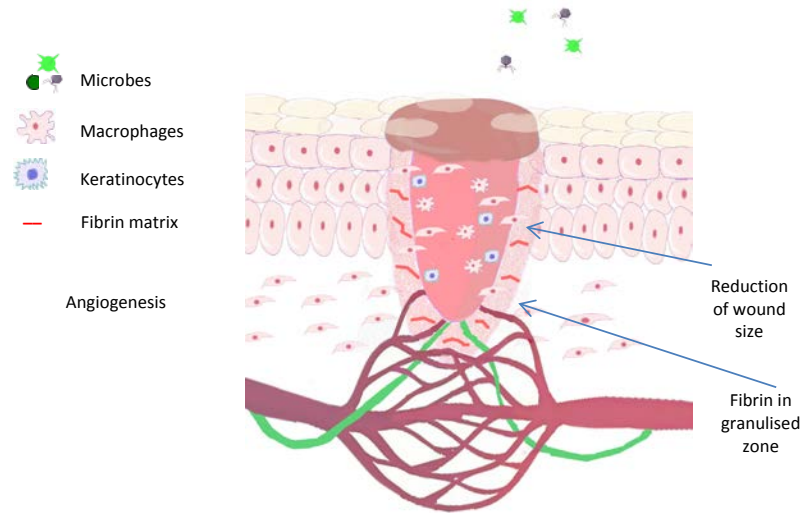

**(d) Regenerative stage**

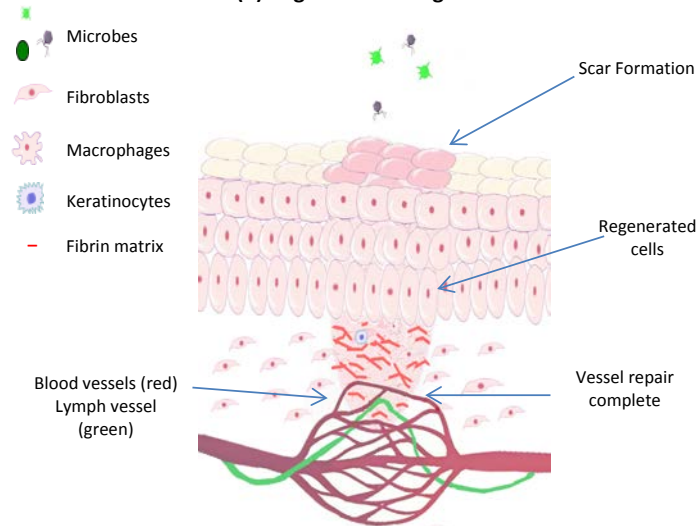

**Table 1.** Important mediators in wound healing process with their respective receptors, cell sources, targets and roles in wound healing.

Factor	Family	Receptors	Cells	Function	Level in acute wounds	Level in chronic wounds	Reference
<b>PDGF</b>	PDGF-BB  <b>Additional:</b> PDGF-AA PDGF-AB PDGF-CC PDGF-DD)	Tyrosine kinase: α-receptor β-receptor	Platelets Fibroblasts Endothelial cells Macrophages Keratinocytes	Chemotaxis  Proliferation of fibroblasts  Promote blood vessel maturation  Matrix deposition Reepithelialisation	Increased levels	Decreased levels	14,26, <a href="#">27</a> , <a href="#">28</a> , <a href="#">29</a> , <a href="#">30</a>
<b>FGF</b>	FGF-2 or bFGF  <b>Additional:</b> FGF-7 FGF-10 KGF  Total: 23 members	Tyrosine kinase: FGFR 1-4	Keratinocytes Mast Cells Fibroblasts Endothelial cells	Angiogenesis  Formation of granulation tissue  Reepithelialisation	Increased levels	Decreased levels	14, <a href="#">26</a> , <a href="#">31</a> , <a href="#">32</a> , <a href="#">33</a> , <a href="#">34</a>
<b>EGF</b>	EGF TGF-α HB-EGF  <b>Additional:</b> Amphiregulin Epiregulin Betacellulin Neuregulins	Tyrosine kinase: EGFR HER2 HER3 HER4	Platelets Macrophages Fibroblasts	Formation of granulation tissue  Reepithelialisation  Increases tensile strength in wound	Increased levels	Decreased levels	14, <a href="#">26</a> , <a href="#">31</a> , <a href="#">32</a> , <a href="#">35</a> , <a href="#">36</a> , <a href="#">37</a>
<b>VEGF</b>	VEGF-A  <b>Additional:</b> VEGF-B VEGF-C VEGF-D VEGF-E PLGF	Tyrosine kinase: VEGFR-1 VEGFR-2 VEGFR-3	Platelets Endothelial cells Macrophages Lymphocytes Neutrophils Keratinocytes	Vasculogenesis  Angiogenesis	Increased levels	Decreased levels	14, <a href="#">26</a> , <a href="#">28</a> , <a href="#">30</a> , <a href="#">32</a> , <a href="#">33</a> , <a href="#">34</a> , <a href="#">35</a> , <a href="#">38</a> , <a href="#">39</a>
<b>TGF-β</b>	TGF-β1	Serine-threonine kinases:	Platelets Macrophages	Angiogenesis Chemotaxis	Increased levels	Decreased levels	14, <a href="#">26</a> , <a href="#">35</a> , <a href="#">39</a> , <a href="#">40</a>

	<b>Additional:</b> TGF- $\beta$ 2 TGF- $\beta$ 3	TGF $\beta$ RI TGF $\beta$ RII	Fibroblasts Keratinocytes	Reepithelialisation  Anabolism of ECM  Collagen production by stimulating fibroblasts  Cellular proliferation and differentiation			35 39 40
<b>Proinflammatory cytokines</b>	IL-1 IL-6  <b>Additional:</b> TNF- $\alpha$ IL-8 IL-11 IL-27	ICAM-1 IL-6R $\alpha$	Monocytes Neutrophils Macrophages Keratinocytes	Chemotaxis  Inflammation (except IL-27)  Reepithelialisation  Collagen synthesis  Synthesis and breakdown of ECM  Regulation of immune response	Increased levels at initial healing stages	Persistent Increased levels	14,26,39,41,42 26 39 41 42

**Abbreviations:** PDGF: Platelet-Derived Growth Factor, FGF: Fibroblast Growth Factor, KGF: Keratinocyte growth factor, EGF: Epidermal Growth Factor; TGF- $\alpha$ : Transforming growth factor-alpha; HB-EGF: Heparin binding EGF, VEGF: (Vascular Endothelial Growth Factor), PLGF: Placenta growth factor, TGF- $\beta$ : (Transforming Growth Factor-  $\beta$ ); IL: (Interleukin); TNF- $\alpha$ : Tumor necrosis factor-alpha

## 1.2. Wound Dressings

Historically, wound dressings were designed to protect the wound site from external environment and played a passive role in healing process [43]. The range of available passive barrier-type wound dressings, *e.g.* gauze and tulle, increased as medical understanding of the wound healing process improved [44]. Such dressings undoubtedly are inexpensive and provide some protection, but being passive, cannot respond to changing wound conditions or deliver medicaments in a controlled or sustained manner to enhance the healing process. For wounds that follow the normal healing process, conventional, barrier-type dressings may be effective; conversely, chronic non-healing wounds can easily become infected thereby failing to progress through the normal stages of healing. Correct clinical management thus becomes imperative to minimise complications during wound healing [1,45].

Ideal dressings not only cover and protect the affected area, but can also create optimal moist environment at the wound site and facilitate healing [46,47,48,49,50]. Advanced wound management strategies involve non-invasive monitoring of healing, pain management and the controlled release of agents capable of promoting regeneration, repair and scar minimisation [51].

The concept of moist healing, as proposed by George Winter, revolutionised the field of wound management, and the focus of wound dressing changed from conventional dry passive products, to responsive moisture-promoting materials [52,53]. Dressing types used to achieve a moist wound healing environment include films, hydrocolloids, foams and hydrogels (Table 2).

**Table 2.** List of commercially available dressings based on the concept of moist wound healing environment.

Type of dressing	Characteristics	Cautions	Proprietary products	Reference
<b>Film dressings</b>	<ul style="list-style-type: none"> <li>• Polyurethane films with an adhesive to hold the dressing</li> <li>• Create moist healing environment</li> <li>• Elastic, durable and conformable</li> <li>• Waterproof and transparent</li> <li>• Semi-permeable to water vapour and gases</li> <li>• Impermeable to bacteria</li> <li>• Impervious to liquids such as wound fluid</li> <li>• No secondary dressing required</li> </ul>	<ul style="list-style-type: none"> <li>• Being non-absorbent, limited use for highly exuding wounds</li> <li>• Being adhesive, newly formed epithelium could be disrupted during removal</li> <li>• Frequently develop leakage channels</li> </ul>	<p>Opsite<sup>®</sup> Films (Smith &amp; Nephew)</p> <p>Tegaderm<sup>™</sup> (3M<sup>™</sup>, UK Plc.)</p> <p>Mepitel<sup>®</sup> Film (Mölnlycke Health Care Limited)</p>	<p>45,<del>50</del> <del>50</del></p>
<b>Hydrocolloid dressings</b>	<ul style="list-style-type: none"> <li>• Moist wound dressing</li> <li>• Capable of absorbing wound exudate</li> <li>• Usually made of polyurethane film with an adhesive mass</li> <li>• Adhesive mass is often composed of gelatin, pectin and sodium CMC which swells on absorbing exudate</li> <li>• Impermeable to water and gases</li> </ul>	<ul style="list-style-type: none"> <li>• Not indicated for infected or heavy exuding wounds</li> <li>• Being opaque difficult to follow the healing process without prior removal</li> <li>• May produce a distinct odour at wound site</li> </ul>	<p>DuoDERM<sup>®</sup> (ConvaTec Inc.)</p> <p>3M<sup>™</sup> Tegaderm<sup>™</sup> hydrocolloid dressing (3M<sup>™</sup>, UK Plc.)</p> <p>Replicare<sup>®</sup> (Smith and Nephew)</p>	<p>55,<del>56</del>,<del>57</del>,<del>58</del> <del>56</del> <del>57</del> <del>58</del></p>
<b>Foam dressings</b>	<ul style="list-style-type: none"> <li>• Bilaminate (or trilaminate) moist wound dressing with varying thickness</li> <li>• Excellent absorption capacity</li> <li>• Can expand and conform to wound shape</li> <li>• Easy to remove</li> <li>• Can be loaded with antimicrobials and other active agents</li> </ul>	<ul style="list-style-type: none"> <li>• Not suitable for low exuding wounds</li> <li>• Frequent change may be required for heavy exuding wounds</li> <li>• May cause maceration on saturation with exudate</li> </ul>	<p>Mepilex<sup>®</sup> and Mepilex Ag<sup>®</sup> (Mölnlycke Health Care)</p> <p>Allevyn (Smith and Nephew)</p> <p>Aquacel<sup>®</sup> (ConvaTec Inc.)</p> <p>Cutimed<sup>®</sup> Siltec B (BSN medical Inc.)</p> <p>Biatain<sup>®</sup> Silicone Ag (Coloplast Ltd.)</p>	<p>59,<del>60</del>,<del>61</del> <del>60</del> <del>61</del></p>
<b>Hydrogel dressings</b>	<ul style="list-style-type: none"> <li>• Insoluble aqueous gels as moist wound dressing</li> <li>• Moisture retention and donation properties</li> <li>• Usually non-adhesive</li> </ul>	<ul style="list-style-type: none"> <li>• Some hydrogels are mechanical weak in swollen state but mechanical properties can be enhanced by</li> </ul>	<p>Purilon<sup>®</sup> Gel (Coloplast Ltd)</p> <p>Derma-Gel (Medline Ind. Inc.)</p> <p>Intrasite<sup>®</sup> Gel (smith &amp;</p>	<p>3,<del>61</del>,<del>62</del>,<del>63</del> <del>61</del> <del>62</del> <del>63</del></p>

---

<ul style="list-style-type: none"> <li>• so easy to remove</li> <li>• Can be loaded with antimicrobials and several active wound healing agents</li> <li>• Can be smart and stimuli responsive</li> <li>• Can be injected</li> <li>• Can be crosslinked <i>In situ</i></li> </ul>	<ul style="list-style-type: none"> <li>• copolymerisation with appropriate polymer(s).</li> <li>• May cause maceration after accumulation of exudate</li> <li>• May require secondary dressing</li> </ul>	<p>Nephew)</p>
---	---	----------------

---

In addition to the above examples of commercially available dressings, there is a plethora of wound dressing products available on the market today, aiming at promoting wound healing, including Adaptic Touch<sup>®</sup> (a non-adhesive silicone dressing by Systagenix Wound Management Limited), ALGICELL<sup>®</sup> and Algosteril<sup>®</sup> (an alginate dressing by Derma Sciences Inc. and calcium alginate dressing by Smith & Nephew, UK respectively), Altrazeal<sup>™</sup> (by ULURU Inc., a white wound filler powder dressing that transforms into a malleable protective dressing on contact with the exudate that fills the wound,), BIOSTEP<sup>™</sup> (by Smith & Nephew, UK, a collagen matrix dressing that optimises wound closure by deactivating excess matrix metalloproteinases) and Drawtex<sup>®</sup> (hydroconductive dressing by Beier Drawtex Healthcare, featuring LevaFiber<sup>™</sup> technology works by capillary, hydroconductive and electrostatic action).

In addition to these dressings, hydrogel dressings are one of the most versatile advanced form of moist wound dressings [64] that are commercially available in different forms. AmeriGel<sup>®</sup> (Amerx Health Care Corp., a hydrogel dressing with moisture sustaining properties), ActiGuard<sup>™</sup> (by Dynarex Inc., a hydrogel sheet dressing that is permeable to air and water vapours enhancing wound breathe) and Intrasite<sup>®</sup> gel (smith&nephew Inc., an amorphous hydrogel dressing that helps in optimising wound environment for re-epithelialisation), are some of the proprietary

hydrogel dressings. The current review would give readers a comprehensive overview of hydrogels as wound dressings. Moreover, the routine scientific approaches of preparing hydrogels for wound management applications, forms of commercially available hydrogel wound products, and the material aspect of hydrogel production with their laboratory characterisation tests are discussed using up-to-date literature.

### **1.3. Hydrogel Dressings**

Hydrogels are composed of water insoluble, cross-linked polymers with a high affinity for aqueous media. These three dimensional polymeric gels have a hydrophilic, porous structure that permits a massive degree of water absorption, several times greater than the original dry weight [3,65,66]. The hydrophilic properties of hydrogels are related to the cross-linking density of polar functional groups such as amide, amino, carboxyl and hydroxyl in the polymer structure [67,68,69,70,71]. Hydrogels offer the unique properties of high water content (up to 99.5%), non-adhesive nature, malleability and a resemblance to living tissues in terms of their biocompatibility [43,63,65,72,73]; all combine to make them an ideal dressing candidate. Moreover, hydrogels display the property of swelling and deswelling reversibly in aqueous solutions, hence their application in a range of sectors including regenerative medicine, drug delivery and the focus of this review, wound management.

Hydrogels help promote wound healing [74] *via* their moisture exchanging activities that develops an optimum microclimate between the wound bed and the dressing [67, 75]. Due to their high moisture content, these dressings also provide a cooling, soothing effect; reduce the pain associated with dressing changes [76]. In addition,

the limited adhesion of hydrogels means that they can be easily removed from the wound, without causing further trauma to the healing tissue [77]. The transparent nature of some hydrogel dressings also allows clinical assessment of the healing process, without the need to remove the dressing.

Hydrogels can be formulated to behave in a stimuli responsive manner [74] so that when loaded with a drug or active biomolecule they are able to control diffusion and release, thus making them truly interactive dressings [78,79]. Some healing agents are hydrophobic in nature and their delivery in hydrophilic environment (wound dressing hydrogel) can be achieved by using solubility enhancing drug carriers like cyclodextrins (CDs) [80]. CDs, a family of cyclic truncated-cone shaped oligosaccharide offers heterogeneous environment i.e. hydrophilic outer surface and hydrophobic inner cavity [80,81]]. CDs have wide pharmaceutical applications in view of their biocompatibility and solubility enhancing properties [82]. In addition, the inclusion of drug in the hydrophobic cavity of CDs, leading to the inclusion complex (IC) formation, offers protective and release modulating properties [83,84]. CD containing hydrogels can be produced in different ways: loading the pre-formulated CD-drug IC during or after crosslinking, grafted on the hydrogels [85] or cross-linking with diglycidyl-ethers [84]. The first approach is a simple but it may have a limitation of unmodulated drug release. In contrast, the release can be controlled with the other approaches [84,86,87]]. Modern therapies where more than one medication with different hydrophilic/hydrophobic nature may benefit, development of CD-based hydrogel with dual drug delivery of hydrophobic drug (attributed to CDs) and hydrophilic compound (selecting polymers with hydrophilic active substance like chitosan), has opened a new scope [82]. The efficacy of these CD-based hydrogels has demonstrated enhanced therapeutic capacity for wound dressing applications

Comment [GA2]: Gupta et al., 2018  
ISBPPB 2018 abstract

Comment [GA3]: Sun et al., 2014

Comment [GA4]: Barragan et al., 2018

Comment [GA5]: Rakmai et al., 2017

Comment [GA6]: Jeong et al., 2018

Comment [GA7]: Lee et al., 2012

Comment [GA8]: Jeong et al., 2018

Comment [GA9]: Jeong et al., 2018

Comment [GA10]: Hoare and Kohane, 2008 not 96 any more

Comment [GA11]: Pinho et al., 2013


Comment [GA12]: Barragan et al., 2018

[84,85,87]. Moreover, hydrogel have been successfully used as a matrix for the fabrication of dressings for the sustained delivery of essential growth factors (Table 1) and healing agents to facilitate wound healing [28,29,31] (Figure 2). All these properties resulted into several proprietary hydrogel wound dressings used in clinical practice for wound management all over the globe. Due to their unique properties, hydrogel dressings are indicated for use in variety of wounds such as, but not limited to, dry wounds with necrotic tissue, burn wounds, diabetic foot ulcers, pressure ulcers, chronic leg ulcers and low to moderately exudating wounds [56,88,89,90]. In spite of the various hydrogel dressing products already in the market, there is still an ongoing research in the area with the aim to further improve the hydrogel dressings covering patient comfort, clinical efficacy and multiple aspects of wound healing.

Comment [GA13]: Lee et al., 2012, Pinho et al., 2013, Jeong et al., 2018

Comment [GA14]: 80,81,82

**Figure 2.** Schematic illustration of (a) Drug loaded homo-polymeric pH responsive hydrogel (b) Hetero-polymeric bioactive material loaded temperature responsive hydrogel (c) Growth factor loaded homo-polymeric hydrogel, with their release trends.

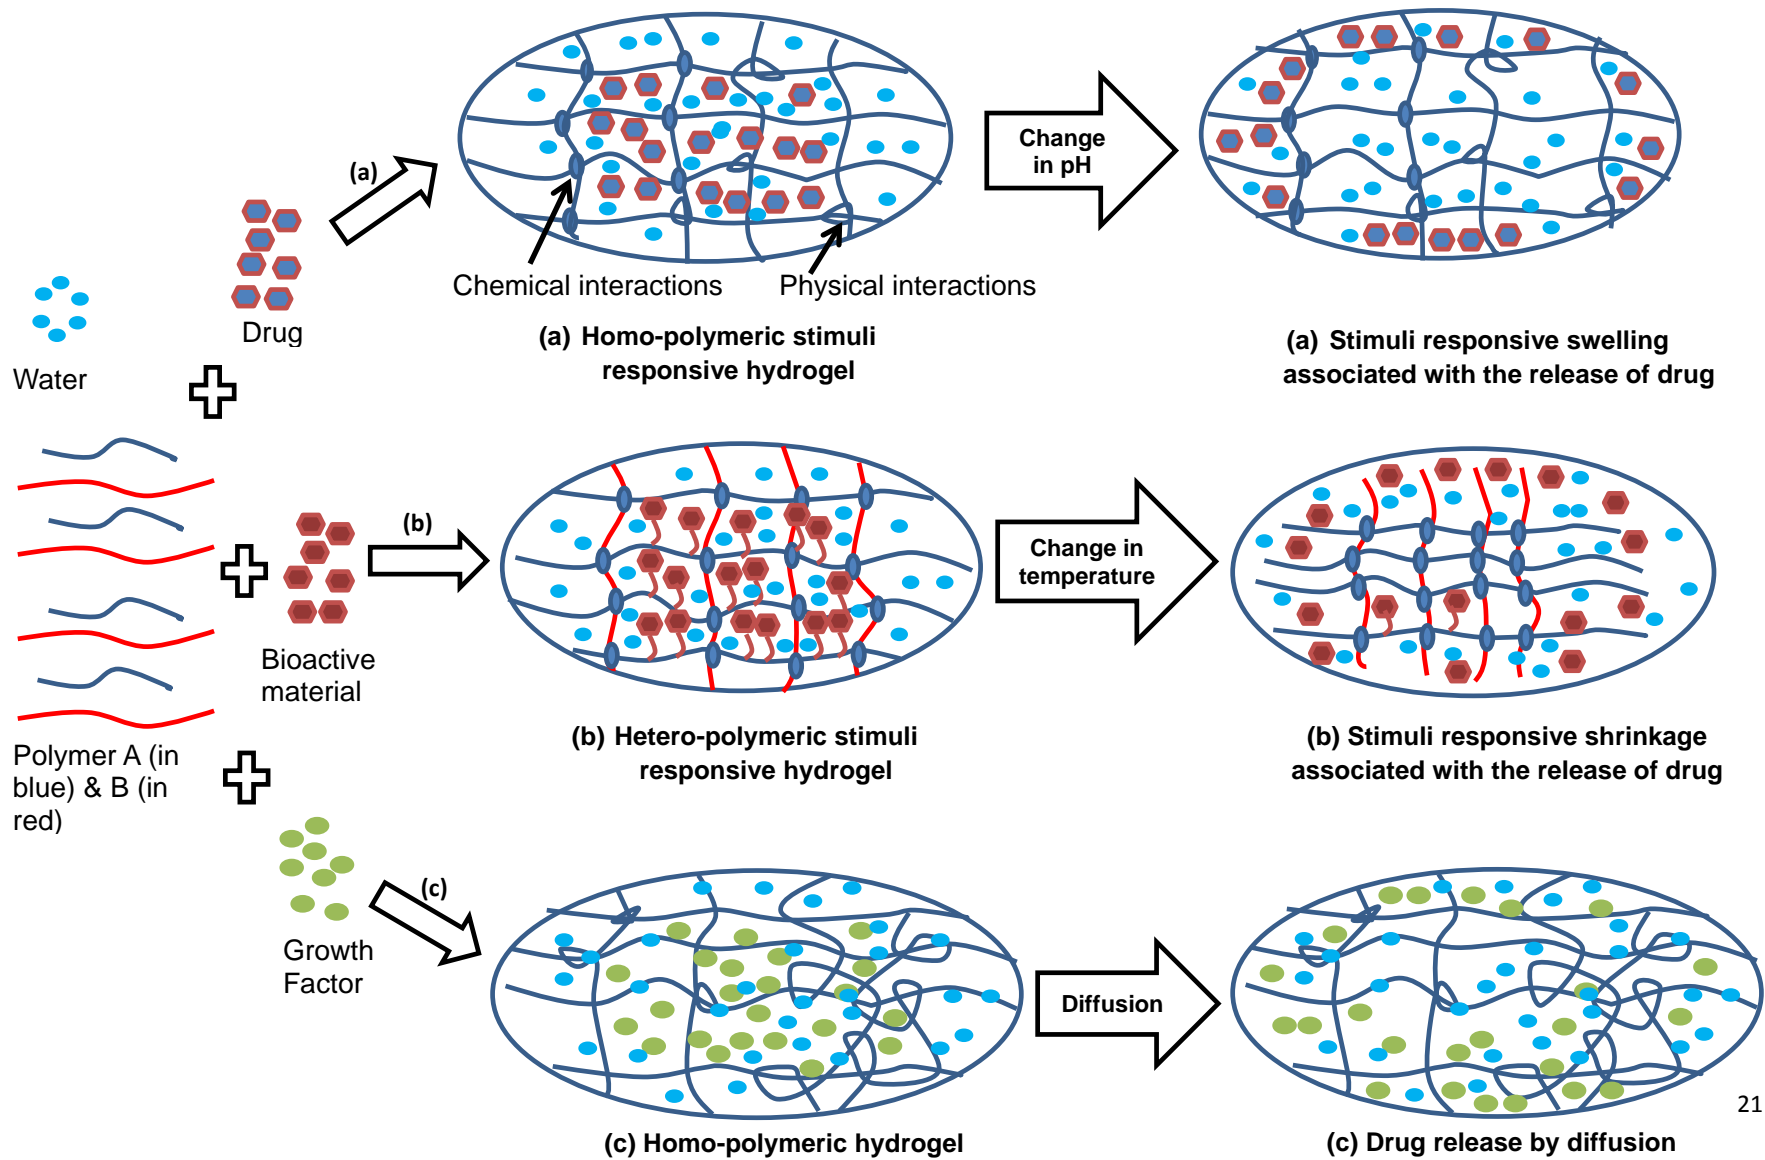

## 2. Preparation of Hydrogels

Hydrogels can be prepared from various natural and synthetic polymers, using a range of different compositions as well as physical and chemical cross-linking techniques. The crosslinks in hydrogels can be due to covalent bonds, ionic interactions, chain entanglements, *etc.*, leading to a variety of physical configurations, chemical arrangements and interactions. Interestingly, it is the very nature of the cross-linkage that determines much of the hydrogel's physicochemical properties and hence eventual applications.

**2.1. Physically crosslinked** hydrogels are formed by the physical linking of polymer chains *via* molecular entanglement, ionic interactions, hydrogen bonding or hydrophobic association [8391]. Several thermodynamic changes *e.g.* heating or cooling of polymer solutions, freeze-thawing, lowering pH, selection of anionic and cationic polymers can result in physical crosslinking between polymeric chains [69, 84,85,8692,93,94]. Preparation of these hydrogels involves relatively mild conditions and simple purification procedures as no toxic chemical crosslinking agents are required during their synthesis; offering them exceptional biological nontoxic, biocompatible properties thus making them ideal matrix for the delivery of therapeutic agents at wound site [66,8795].

### 2.1.1. Ionic interactions:

These hydrogels are formed between ionic polymers crosslinked with multivalent, counter charged species. Polyanionic polymers that are complexed with polycationic polymers form hydrogels by a process of polyelectrolyte complexation, which is also referred to as complex coacervation [8896]. Alginate hydrogel dressings using

divalent calcium cations ( $\text{CaCl}_2$ ) are commonly synthesised by this technique [89,9097,98].

### **2.1.2. Crystallisation:**

Hydrogels for wound management applications can also be synthesised by freeze-thawing. During freeze-thawing of an aqueous polymeric solution, water freezes causing phase separation which leads to the formation of microcrystals [91,9299,100]. Repeated freeze-thaw cycles facilitate reinforcing existing crystals within the structure and offers higher crystallinity and added stability upon swelling [87,9395,101]. Physically crosslinked biocompatible and elastic hydrogels using PVA/PEG polymers [92100] and PVA/sodium alginate [94102], fabricated by consecutive freeze-thaw cycles as a potential wound dressing formulation are examples of this type of gelation.

### **2.1.3. Hydrogen bonding between chains:**

This class of hydrogels can be produced by lowering the pH of aqueous polymer solutions, when carboxylic groups are present on the chains. At acidic pH aqueous polymer solubility is reduced which promotes hydrogen bonding and the formation of hydrogels [95103]. However, these physical networks can easily disperse with the influx of water therefore in addition to these other type of crosslinking can be considered to hold the hydrogel constituents [9686]. Hydrogels with pH sensitive gelation (around pH 6.5) of chitosan can be produced by these physical interactions [97104].

### **2.1.4. Amphiphilic block copolymers:**

These physical hydrogels are made from two chemically different homopolymer blocks one of which is hydrophobic and the other is hydrophilic. These copolymers self-assemble in aqueous media forming hydrogels due to thermodynamic incompatibility between the blocks [98,99,105,106]. Moreover, drugs like antimicrobials can be incorporated in these copolymers and sustained release can be achieved for wound management applications [400,404,107,108]. Thermoresponsive poly( $\epsilon$ -caprolactone)-poly(ethylene glycol) block copolymer hydrogels with potential wound dressing applications are a good example of this category [401,402,403,108,109,110].

#### **2.1.5. Protein interactions:**

With the advancement in biotechnology, hydrogel synthesis by engineering of recombinant proteins has become possible. This new development in the field of material chemistry pioneered by Tirrell and Cappello [404,405,111,112] allows to control the structural and functional design of protein block thus preparing the physically crosslinked hydrogels with desirable biological, physical and mechanical properties. These biopolymeric protein based hydrogels primarily assemble by protein-protein interactions or aggregation of polypeptides by phase (temperature) transitions [406,113]. It can be foreseen that these hydrogels hold a strong potential in wound management. Fabrication of protein engineered bioactive collagen-mimetic protein (eCol<sub>GFPGER</sub>) with PEG based matrix hydrogel dressings with a potential of wound healing in humans is an innovative approach in the field of wound management [407,114].

**2.2. Chemical crosslinked** hydrogels are formed by covalent linkages resulting in high mechanical strength networks. These can be synthesised by chain growth

polymerisation, addition and condensation polymerisation and high energy irradiations (gamma ray or electron beam).

### **2.2.1. Crosslinking by chain growth polymerisation:**

It includes three stages: initiation, propagation and termination. Generation of free radical site by suitable reaction initiator initiates the polymerisation process followed by chain elongation by the addition of low molecular weight monomeric building blocks. The elongated polymer chains are randomly crosslinked by the cross-linking agent leading to the hydrogel formation [408,115]. Hydrogel of 2-acrylamido-2-methylpropane sulfonic acid sodium salt (AMPS- $\text{Na}^+$ ) using potassium persulfate as a free radical initiator and ethylene glycol dimethacrylate as a crosslinking agent can be synthesised by redox initiation via free radical polymerisation for wound dressing applications [409,116]. Chemically crosslinked hydrogel of AMPS with AMPS- $\text{Na}^+$  prepared by using 4,4-azo-bis(4-cyanopentanoic acid) as photo-initiator and N,N'-methylene-bisacrylamide as a cross-linking agent demonstrated optimum water absorption and retention properties for wound management applications. Moreover, their flexible and transparent nature with good skin adhesion properties advocates their potential biomedical applications [410,117].

### **2.2.2. Crosslinking by chemical reactions of complementary groups:**

Hydrophilic polymers have functional groups like  $\text{COOH}$ ,  $\text{OH}$  and  $\text{NH}_2$  which can be utilised for the hydrogel formation. These pendant functional groups with complementary reactivity (amine-carboxylic acid or isocyanate- $\text{OH}/\text{NH}_2$  reaction or Schiff base formation) can establish covalent linkages between polymer chains leading to the hydrogel formation using crosslinking agents [411,412,413,118,119,120]. Antibacterial alginate-chitosan hydrogel wound dressings

can be synthesised by the Schiff based reaction between aldehyde group of oxidized alginate and amino group of carboxymethyl chitosan [444118]. Injectable *in situ* chitosan-hyaluronic acid hydrogels [444121] for wound applications are another example with gelation attributing to Schiff base between amino group of carboxymethyl chitosan and aldehyde group of aldehydic hyaluronic acid. Being injectable, these hydrogel dressings hold an added advantage of easy and comfortable application with high conformability without wrinkles which could lead to improved patient compliance.

### 2.2.3. Crosslinking by using high energy radiations:

Cross-linking by radiations is widely used to polymerise unsaturated compounds for hydrogel synthesis since it is devoid of the use of toxic chemical crosslinking agents and is a cost effective technique as separate sterilisation of hydrogel formulation can be avoided. On exposure to high energy radiations, radicals are formed on polymer chains in an aqueous solution which initiates free radical polymerisation. Recombination of these radicals on different polymer chains lead to the formation of covalent crosslinked hydrogels [66,8896]. Silver nanoparticles loaded AMPS-Na<sup>+</sup> hydrogels [445122], PVA/gum acacia [446123] and nanosilver/gelatin/carboxymethyl chitosan hydrogels synthesised by gamma (cobalt-60) irradiation technique are examples of potential antimicrobial hydrogel wound dressings [447124].

### 2.2.4. Crosslinking by thiol-ene click reaction:

The reaction of thiols (nucleophile) to electron-rich alkenes leading to the production of thioether polymer networks is a weapon of choice for hydrogel preparation owing

Comment [GA15]: Hennink and Nostrum 2012

to their biological inertness, rapid reaction rate and controlled release properties. Dictated by the functional groups and reaction conditions, the reaction mechanism could be thiol-Michael click reaction or radical-mediated thiol-ene reaction [125]. Synthesis of gelatin/poly(ethylene glycol) hydrogels for the delivery of immunomodulatory molecules like cytokines and growth factors through mesenchymal stem cells (MSC) carriers [126], epidermal growth factors loaded heparin-based hydrogels [127], and poly(urethane-acrylate) based antimicrobial hydrogel wound dressings [128] for wound management applications are good examples of thiol-ene reactions.

Comment [GA16]: Kharkar et al., 2016

Comment [GA17]: Xu et al., 2013

Comment [GA18]: Goh et al., 2016

Comment [GA19]: Gharibi et al., 2017

### 3. Hydrogel dressing products:

There are many different types of wounds with multitude of different symptoms, including necrotic, sloughy, granulating and epithelialising that vary in size, shape and thickness. Understanding the purpose and principle of dressing formulations for these differing applications helps to match the correct dressing and wound combination.

Hydrogel dressings are indicated for the treatment of a variety of wound types, with precise selection of formulation ultimately based on clinical application:

#### 3.1. Amorphous hydrogels:

Lacking a fixed shape, these hydrogels can be evenly applied over the wound using an applicator and being amorphous, these would mould into the shape of wound defect easily. These are specifically indicated in the treatment of uneven or cavity wounds that cannot be easily covered with fixed, definite shape dressings. Examples of commercially available products include: 1) Aquasite<sup>®</sup>, an amorphous, glycerine-

based hydrogel dressing [Derma Sciences Inc.], and 2) Intrasite<sup>®</sup> gel, a partially hydrated, amorphous propylene glycol hydrogel [Smith & Nephew, UK].

### **3.2. Impregnated hydrogel gauze dressings:**

Used for partial or full thickness wounds where sterile packing of the wound bed is required, these formulations combine the advantages of hydrogels with non-woven dressings. Impregnated gauze dressings are saturated and/or permeated with an amorphous hydrogel and are commercially available as gauze pads, non-woven sponges and strips of different sizes. Commercially available products under this category are: 1) Aquasite<sup>®</sup> impregnated gauze dressing, a 100% cotton gauze pads incorporated with a hydrogel [Derma Sciences Inc.], and 2) Intrasite<sup>®</sup> conformable, hydrogel impregnated gauze dressings [Smith & Nephew, UK]. These dressings are available in various sizes and are indicated for use in necrotic, sloughy and granulating full thickness wounds.

### **3.3. Sheet hydrogel dressings:**

Consisting purely of hydrogel, these dressings can be cut into the required size and shape to fit the wound. Hydrogel sheet dressings are indicated for the treatment of deep cavity and partial thickness wounds (e.g. ulcers, including venous and arterial, pressure sores, skin donor sites, surgical incisions, 1<sup>st</sup> and 2<sup>nd</sup> degree burns). Aquasite<sup>®</sup> hydrogel sheet dressing, glycerine based hydrogel formulations [Derma Science Inc.] and Flexigel<sup>®</sup> sheet, polyacrylamide based hydrogel sheet dressings [Smith & Nephew, UK] are commercially products available in different sizes (e.g. 2"x2" and 4"x4") and can be easily cut to fit wound. These act as advanced wound dressing by keeping the wound bed moist thus offering soothing effect and facilitate wound healing as well as providing physical barrier between wound and external

environment. Moreover, being transparent, these sheet dressings allow easy monitoring of healing process.

#### **4. Polymers suitable for hydrogel wound dressings:**

Some polymers due to their physicochemical and biocompatible properties are extensively used in biomedical applications. Most commonly used polymers used for fabricating hydrogel for wound dressing applications are discussed below. Moreover, other commonly used polymers with wound dressing applications are listed in Table 3.

##### **4.1. Poly(vinyl alcohol) (PVA)**

PVA being biocompatible, transparent and capable of maintaining moist environment has attracted application in wound care [448,449,129,130]. PVA chains can be crosslinked to produce PVA hydrogels by variety of techniques including freeze-thawing cycle, electron beam irradiation and using cross linkers like glutaraldehyde [53]. Hwang *et al.*, (2010) [420,131] employed a freeze-thaw technique to produce a gentamicin-loaded PVA-dextran hydrogel dressing. The authors suggested that the presence of dextran in the hydrogels enhanced the elasticity, swelling ability and water vapour transmission rate (WVTR) of hydrogel. Moreover, dextran favours the crystallisation of PVA, thus producing a more uniform, homogenous gel structure. *In vitro* test results confirmed the hydrogel formulated with 2.5% PVA, 1.13% dextran and 0.1% gentamicin was haemocompatible thus suitable for wound management applications. Moreover, *in vivo* (rat model) tests revealed enhanced healing with greater wound size reduction of a full thickness surgical excision wound of the dorsum with gentamicin-loaded-PVA-dextran hydrogels compared to the foam dressing (Medifoam™) and gauze dressing. The re-epithelialisation rate of

gentamicin loaded resulting hydrogel was significantly higher ( $98\pm 2\%$ ) than conventional foam dressing ( $74\pm 14\%$ ) which supporting its potential wound dressing application.

Sodium ampicillin containing PVA-Sodium Alginate (PVA-SA) hydrogel membranes for wound dressing applications were synthesised by Kamoun *et al.*, (2015) [94102].

Comment [GA20]: Kamoun *et al.*, (2015)

The authors achieved physical crosslinking (entanglement) between PVA and different content of SA by repeated freezing-thawing cycles. *In vitro* protein adsorption test was performed to determine the ability of the hydrogels with regards to cleansing the secreting lesions and the results suggested an increase in bovine serum albumin (BSA) adsorption from  $0.7\text{-}1.8\text{mg}/\text{cm}^2$  with an increase in SA content from 0-75% (w/w). These membranes demonstrated high haemocompatibility and broad antibacterial activity suggesting their potential application as an active biodegradable hydrogel dressing in wound care. In another study, PVA based hydrogel dressing was developed *in situ* by co-enzymatic reaction using glucose present in wound exudate to trigger crosslinking. Glucose oxidase (GOx) and horseradish peroxidase (HRP) were used to catalyse the hydrogelation process. GOx oxidised glucose to  $\text{H}_2\text{O}_2$  which in the presence of HRP was taken by phenolic hydroxyls of the PVA derivative (PVA-Ph) leading to the hydrogel formation. The authors presented *in vivo* findings suggesting significantly faster cure of full-thickness wounds (rat model) with 77% and 96% wound closure at 7 and 10 days of treatment, respectively compared to only 27% at day 7 and 70% at day 10, with commercially available hydrogel dressing [121132].

#### 4.2. Poly(N-vinyl-2-pyrrolidone) (PVP):

PVP, a well-known synthetic polymer due to its biocompatible nature has attracted several biomedical applications including wound management. Nu-Gel<sup>®</sup> (Systagenix) and Neoheal<sup>®</sup> (Kikgel) are PVP based proprietary hydrogel products indicated for use in first and second degree burns, severe sun burns, partial thickness wounds, ulcerations and bedsore. PVP undergoes crosslinking under ionising radiation, resulting in transparent hydrogels but these hydrogels have poor mechanical properties with limited swelling. It's swelling behaviour and mechanical properties can be enhanced by blending it with other polymers such as polysaccharides [122,123,124,125,126,133,134,135,136,137]. The use of ionizing radiations is considered to be a favourable tool, wherever feasible, for hydrogel formation (and sterilisation) due to easy process control, minimal wastage, low cost and no chemical crosslinkers requirement [123,127,134,138].

Fechine *et al.*, 2004 [128,139] reported an approach to synthesis PVP hydrogel using safer, portable and less expensive UV radiation ( $\lambda_{\text{max}}$  254nm) technique. They produced hydroxyl radicals from the photolysis of H<sub>2</sub>O<sub>2</sub> and these radicals were reacted with PVP giving rise to macroradical polymer chains which underwent recombination leading to the hydrogel formation. The hydrogel produced demonstrated *in vivo* cytocompatibility with satisfactory low inflammation index in rabbit model (72hr direct contact with rabbit skin) hence classified as non-irritating material for wound management purposes.

Jovanovic *et al.*, (2011) [129,140] reported an approach to synthesise antimicrobial PVP hydrogels using gamma radiation to achieve gelation. Antimicrobial properties in these hydrogels are attributed to silver nanoparticles produced *in situ* in PVP hydrogel matrix by reduction of silver nitrate with radiolytic products of water up on gamma irradiation. These nanocomposite hydrogels exhibited high elasticity, good

mechanical properties and good swelling capacity and may be tailored for potential wound dressing applications.

Another attempt of fabricating antimicrobial silver nanoparticles (AgNP) loaded PVP based blend hydrogel using gamma radiations was made by Khampieng *et al.*, 2018 [130,141] for wound management of chronic wounds. The blend of PVP with alginate and chitosan in the ratio of 10:1.2:1.8 respectively enhanced the swelling and mechanical properties making these hydrogels suitable for dressing applications. When compared to three commercially available dressings (Acticoat™, Algivon® and Suprasorb® A + Ag), these hydrogels (10mM AgNP concentration) showed superior cytocompatibility with higher cell viability against mouse (112.64±4.66%) fibroblasts (L929), human dermal fibroblast (89.47±1.11%) and human keratinocytes (HaCaT) cells (105.35±4.52%). Moreover, the maximum swelling behaviour (2267±109%) of these resulting hydrogels was superior to Acticoat™ (362±66%). These findings suggested their greater capability of absorbing wound exudate thus making them a potential candidate for chronic wounds including pressure ulcers.

#### 4.3. Poly(ethylene glycol) (PEG):

PEG is a polyether which attracted a wide interest in the biomedical applications including wound management due to its transparent, non-toxic, non-immunogenic, biocompatible and biodegradable properties [131, 132,142,143]. PEG fumarate [133,144] and PEG acrylates like PEG diacrylate (PEGDA) [134,135,145,146], PEG dimethacrylate (PEGDMA) [136,147] and PEG methyl ether methacrylate (PEGMEMA) are some of the commonly used acrylates in hydrogel formation for biomedical applications. Due to its featured biological properties, PEG has been

used in proprietary products like Aquaflo™ (Covidien), Neoheal® (Kikgel) and AmeriGel® (Amerx Health Care Corp.) hydrogel wound dressings.

Since chronic wounds are associated with alkaline pH, with an aim to restore the elevated pH to the physiological pH (7.4), in order to facilitate healing, Koehler *et al.*,

2017 [134,142] fabricated a pH-modulating acidic PEGDA/Alginate hydrogel dressings containing acrylic acid (AA). In addition to controlling the alkaline pH neutralisation, AA enhanced the swelling capacity of the hydrogels. PEGDA/AA/alginate hydrogels with 0.25%AA demonstrated superior mechanical strength, biocompatibility and enhanced cell migration velocity ( $19.8 \pm 1.9 \mu\text{m h}^{-1}$ ) in a 2D cell migration assay leading to a complete wound closure. Also, the ingrowth of keratinocytes increased by 164% (3D Human skin constructs and Healing assay) compared to untreated control. Chen *et al.*, 2013 [48] prepared a PEG/chitosan hydrogel dressing by using PEG diacid (PEG with carboxylic acid groups at both ends) crosslinked to chitosan by way of ester and amide linkages. Authors reported that PEG/chitosan with the mole ratio of carboxylic acid from PEG diacid (PEG molecular weight 1000Da) to amine group from chitosan of 90/10 offered good mechanical properties and appropriate degradation rate. Also, *in vivo* wound treatment studies (mice model) revealed the capability of these hydrogels to suppress inflammation, with fewer inflammatory cells, enhance re-epithelialisation and increased angiogenesis thus supporting their potential use as a biomaterial for wound dressings.

Comment [GA21]: Koehler *et al.*, 2017

In another study, Dong *et al.*, 2014 [137,148] formulated a wound dressing hydrogel using PEG-based multifunctional hyperbranched copolymer crosslinked with thiolated hyaluronic acid (HA-SH) with adipose-derived stem cells (ADSC). These polymers stay as a solution at room temperature while they undergo *in situ*

crosslinking (thiol-vinyl Michael addition between vinyl groups on copolymer and thiol on HA-SH) at body temperature, forming a stable, non-adhesive and bioactive hydrogel (within 8 minutes) at the wound site. Being injectable, these can be easily and effectively applied to any wound shape and size. Although *in vivo* studies (rat model) revealed that these hydrogels resisted wound contraction to some extent but there was a strong evidence of their angiogenesis enhancing ability.

#### 4.4. Poly(2-hydroxyethyl methacrylate) (PHEMA):

PHEMA was the first hydrogel used in the production of soft contact lenses due to its inert nature, biocompatibility, excellent mechanical strength and high water imbibing properties [138149]. In addition to its biomedical application as a contact lens material, due to its exceptional physicochemical properties and accepted *in vivo* tolerance, it has attracted its use in wound management as a hydrogel dressing material [139150].

Halpenny *et al.*, 2009 [140151] reported the use of PHEMA in the fabrication of the bactericidal light sensitive hydrogel wound dressing. With inherent wound healing properties and to avoid potential emergence of antibiotic resistance, nitric oxide (NO) was selected as an antimicrobial agent. In order to deliver NO to a desirable site with controlled release, authors developed photoactive NO donors (nitrosyls) which were incorporated into polyurethane that was covalently incorporated into pHEMA hydrogel. In order to enhance the antimicrobial activity of these hydrogels, H<sub>2</sub>O<sub>2</sub> or methylene blue were used as auxiliary growth attenuators. When these hydrogels were tested against *P. aeruginosa* and *E. coli*, significant antimicrobial activity was recorded. Authors proposed that this approach was superior to washing the wound site with 3% H<sub>2</sub>O<sub>2</sub> solution. This study demonstrates the futuristic approach of

fabricating hydrogels with an added advantage of controlled release of antimicrobial by illuminating (stimuli) the dressing (exposure to light) from time to time to maintain antiseptic conditions at the wound site.

Singh and Dhiman, 2015 [75] produced antibiotic (moxifloxacin) containing PHEMA-based copolymeric hydrogel dressings using carbopol and gum acacia by free radical polymerisation method, with potential wound dressing applications. The permeability test results showed that these are permeable to oxygen and impermeable to microbes present in open environment. Moreover, their high fluid uptake ( $7.22 \pm 0.26$ g per gram of gel) and retaining property makes these hydrogel dressings suitable for application in moderate to high exudative wound with potentially 3-5ml exudate per  $10\text{cm}^2$  per day. These hydrogels have been proposed to be haemocompatible (0.95% haemolytic effect) thus validating their wound management applications. Their low albumin absorption ( $0.19 \pm 0.02$ mg  $\text{cm}^{-2}$ ) which could be attributed to highly hydrophilic nature of gum acacia, also favours its wound dressing application. Formulations with antioxidant activity may help to reduce oxidative stress at the chronic wound site thus promote healing. The results from the antioxidant activity [Folin–Ciocalteu (F–C) reagent assay] and superoxide radicals scavenging ability ( $64.21 \pm 2.70\%$ ) were found promising. *In vivo* test (mouse model) results revealed that unlike gauze dressings, the resulting hydrogels could be removed easily removed from wound site without causing trauma. Moreover, wounds treated with these hydrogels revealed enhanced healing with well organised fibroblasts and angiogenesis compared to open untreated wounds. All these properties advocate their wound management applications as wound dressings.

Controlling the microbial bioburden is a major challenge in chronic wound healing and the introduction of antimicrobial agents in the polymeric materials with potential

biomedical applications is a common practice to tackle this challenge. Amongst different antimicrobial agents, silver is widely used due to its strong antimicrobial activity [3]. Several methods have been reported in literature to produce silver nanoparticles [141,142,143,144,152,153,154,155]. Siddiqui *et al.*, 2016 [145,156] made a successful attempt to produce antimicrobial nanocomposite PHEMA hydrogels with silver nanoparticle (AgNPs) using *in situ* radical polymerisation. These hydrogels exhibited good thermomechanical properties with potential wound management applications. In another study, with the aim of controlling bacterial bioburden at the wound site whilst maintaining the moist environment, Di *et al.*, 2017 [146,157] synthesised transparent antimicrobial PHEMA based hydrogels coated with AgNPs reduced by sodium hydrogen borate. Authors added bacterial cellulose to PHEMA to improve its flexibility and hydrophilic properties. These hydrogels were tested against two opportunistic microbial strains, *Escherichia coli* (*E. coli*) and *Staphylococcus aureus* (*S. aureus*). Disc diffusion results revealed antimicrobial activity with clear zone of inhibitions (ZOI) measuring  $0.25 \pm 0.15$ cm and  $0.50 \pm 0.15$ cm respectively for the tested strains. Moreover, these findings were confirmed with colony forming unit (CFU) method with 99% and 90% reduction in CFU count against the respective tested strains, after 24h. Furthermore, these hydrogels exhibited rapid water absorption which would minimise the detrimental effect of exudate on wound site. Being transparent, these hydrogels would allow monitoring of the healing process without the need of removing the dressing. All these properties, along with low toxicity results advocate its potential application in wound management.

#### 4.5. Poly(n-isopropylacrylamide) (PNIPAM):

PNIPAM is a smart polymer with amide and propyl moieties in its monomeric structure responsible for its temperature dependent volume phase transition (VPT at 34°C). Its lower critical solution temperature (LCST) is slightly lower (32°C) than VPT temperature. Being nontoxic, biocompatible and with phase transition close to the human body, it has attracted wide biomedical applications [147,148,149,158,159,160].

Jiang *et al.*, 2012 [159,161] synthesised thermoresponsive antimicrobial PNIPAM wound dressing hydrogels crosslinked using PEGDA by free radical polymerisation using ammonium persulfate (APS) and N,N,N',N'-tetramethylethylenediamine (TEMED) as initiators. Cell interaction properties of PNIPAM were enhanced by using acryloyl-lysine (A-Lys), which is known to improve cell adhesion and proliferation. Polyhexamethylene biguanide (PHMB) with low cellular toxicity and broad spectrum activity was used as an antimicrobial agent. *In vivo* wound healing studies (rat model) in normal and infected (with *Pseudomonas aeruginosa*) wounds demonstrated enhanced healing with accelerated wound closure on day 4, with 21.66±7.94% wound size reduction in PHMB-loaded hydrogels compared to untreated control (5.92±4.11%). Furthermore, decrease in surface bacterial concentration with PHMB-loaded-PNIPAM hydrogels was also observed as compared to untreated control group.

The bone marrow mesenchymal stem cells (BMSCs) are known to secrete growth factors like TGF-β and FGF and accelerate wound healing in healthy skin however due to increased protease secretion by high levels of cytokines in inflammatory environment of chronic wounds, their activity can be compromised. In order to fully harvest the benefit of delivered BMSCs at the wound site, chronic inflammation

needs to be controlled which would ultimately lead to protease inhibiting activity [151,152,162,163]. Chen *et al.*, 2015 [154,162] designed thermosensitive biocompatible PNIPAM hydrogel dressings using poly(amidoamine) as a biodegradable cross-linker, to deliver the encapsulated BMSCs to the diabetic ulcers. *In vivo* (diabetic mice model) immuno-histochemical studies using CD86 to mark M1 macrophages and CD163 for M2 macrophages on day 5 and 7, revealed that the hydrogel treatment inhibited chronic inflammation at the wound site as compared to untreated control group. Moreover, the hydrogel enhanced the secretion of growth factors (TGF- $\beta$  and FGF) by BMSCs resulting in the formation of granulation tissue, angiogenesis, ECM secretion and re-epithelialisation, leading to healing of wounds in diabetic mice model. These findings provide guidance and evidence of efficiency of these hydrogels in treating diabetic ulcers.

#### 4.6. Alginate:

Alginate, a natural polysaccharide derived from marine brown algae and some soil bacteria has attracted wide biomedical application including wound management due to its hydrophilic, biocompatible and non-toxic nature [89,153,154,155,156,97,164,165,166,167]. Its exceptional wound healing properties resulted in its use for fabricating commercially available hydrogel dressings like Purilon<sup>®</sup> Gel (Coloplast Ltd.) and Nu-Gel<sup>™</sup> Hydrogel with Alginate (Systagenix Wound Management Ltd.). Alginate has an ability to form hydrogels by addition of divalent cations like Ca<sup>2+</sup> which binds to guluronate blocks of alginate chains enabling ionic cross-linking between guluronate block of adjacent alginate chains in the so called egg-box cross-linking model leading to gel formation [157,158,159,168,169,170]. In case of loss of the divalent cationic cross-linker, the alginate dressing can easily degrade but this issue is commonly overcome by cross-

Comment [GA22]: Rezvanian et al., 2016

linking (ionic or covalent) alginate with other polymers like PVA, gelatine, chitosan etc. [43]. Balakrishnan *et al.*, 2005 [~~160~~171] made an attempt to synthesise a hydrogel wound dressings (in situ) by periodate oxidation of sodium alginate (SA) resulting in alginate dialdehyde (ADA) and subsequently reacting it with gelatine (G) using borax.  $\epsilon$ -amino groups of lysine or hydroxylysine groups of gelatine complexed with available aldehyde, facilitated by borax, resulting in a crosslinked hydrogel. In addition to accelerating this Schiff's base formation, borax acted as an antiseptic. This hydrogel formulation demonstrated optimum WVTR ( $2686 \pm 124 \text{ g/m}^2/\text{day}$ ) and water absorptivity. Moreover, the rate of re-epithelialization, *in vivo* (rat model), was significantly enhanced ( $90.38 \pm 9\%$ ) in wound treated with hydrogel dressings compared to gauze dressings ( $81.65 \pm 9\%$ ). Furthermore, wound size was significantly reduction in wounds treated with these dressings ( $95.3 \pm 5\%$ ) compared to gauze dressings ( $75.5 \pm 5\%$ ), suggesting their potential application in wound management.

Comment [GA23]: Balakrishnan *et al.*, 2005

In another study, Saarai *et al.*, 2012 [~~164~~172] selected SA and G polymers with the same objective of obtaining a moist, elastic and biocompatible hydrogel wound dressing. They used various SA and G concentrations to underpin the correct blend ratio of SA and G to produce hydrogel with optimum physicochemical properties for wound management applications. Based on the results findings, the authors proposed SA/G 50/50 ratio to be optimum producing a hydrogel with desirable viscoelastic and absorption properties for wound management application.

#### 4.7. Chitosan:

Chitosan is a linear natural polysaccharide derived by alkaline N-deacetylation of chitin, obtained from exoskeleton of crustacean like crab, lobster and shrimp [~~162~~,

~~163,~~ ~~164~~ 173,174,175. Due to its biocompatibility, haemocompatibility, biodegradable nature and featured haemostatic, antimicrobial (bacteriostatic and fungistatic) and wound healing properties [48,~~165,166,167~~ 176,177,178], it is considered fit as wound dressing material. Chitosan can be used to produce membrane, sponge, scaffold and it also has hydrogel forming ability. However, a hydrogel formulation would be the most suitable form as it is able to protect, interact, contract the wound and facilitate wound healing by developing optimum moist healing environment [~~168~~ 179]. Chitosan can get deformed easily through external stress but this challenge can be overcome by blending it with suitable polymers to enhance its mechanical properties for fabricating wound dressing [48].

Ribeiro *et al.*, 2009 [~~167~~ 178] developed an antimicrobial chitosan hydrogel dressing using lactic acid to induce stoichiometric protonation of the  $-NH_2$  sites of chitosan followed by exposure to ammonia fumes (later removed). The hydrogel formation mainly involved hydrogen bonding and physical entanglement of polymer chains. The hydrogel produced was claimed to be porous, favouring gaseous ( $O_2$  and  $CO_2$ ) exchange and preventing build-up of exudate. *In vitro* and *in vivo* experiments confirmed the cytocompatibility and histocompatibility (local and systemic) of the biomaterial. MTT assay results using fibroblasts cells from rat skin seeded with the resulting hydrogel for 24h confirmed cytocompatible nature of this biomaterial. The application of these hydrogels in dermal burn wounds was evaluated by inducing full-thickness transcutaneous dermal wounds in rats. *In vivo* histological studies further confirmed the biocompatibility of these hydrogels as no inflammation or specific pathological abnormalities were observed during the test period. Macroscopic analysis results of wounds treated with these hydrogels revealed considerably smaller wound bed compared to control (PBS treated). Clinical application potential

of these hydrogels for wound management needs to be further evaluated by undertaking advanced studies.

In another study, Wang *et al.*, 2012 [468,179] reported the development of chitosan, honey and gelatine hydrogel sheets for burn wounds. The authors produced sheets by varying content of chitosan (not more than 0.5 wt%) and honey (not more than 20 wt%) but keeping the amount of gelatin constant (20 wt%) and studied the physicochemical and functional characterisation of these hydrogel sheets on burn wounds. Chitosan and honey showed a positive synergistic effect as antibacterials in these dressings. Hydrogel formulation with chitosan (0.5 wt%), honey (20 wt%) and gelatin (20 wt%) was reported to be the optimal dressing due to its soft moist nature and excellent *in vitro* antimicrobial activity (100% inhibition rate) against *E. coli* and *S. aureus*. Biocompatibility of the resulting hydrogels was established by *in vivo*, acute oral toxicity study (mouse model) and dermal irritation test (rabbit model) with no noticeable toxic symptoms or skin irritation during set time points of upto 48h. Wound healing study (rabbit model) revealed that throughout the study at each set time point (on day 4, 8 and 12) hydrogel formulations demonstrated higher wound contraction compared to commercially available MEBO<sup>®</sup> ointment and untreated control. The complete recovery of the burn wound was achieved in around 12 days with hydrogel dressings compared to 14 days with MEBO<sup>®</sup> treated group and 17days in the control group concluding a faster healing with the hydrogels.

Comment [GA24]: Wang *et al.*, 2012

#### 4.8. Starch:

Starch is one of the most abundant natural polysaccharide composed of two different polymers, namely amylose and amylopectin. Being economical, non-toxic, biocompatible and biodegradable, native starch has a potential as a wound

management material but its highly hydrophilic nature and relatively poor mechanical properties have limited its application. These problems can be overcome by either combining it with other polymer to make blend hydrogels [469,180] or by chemically modifying native starch to improve its properties for biomedical applications. Oxidised starch [470,174,181,182] and hydroxyethyl starch (HES) [85] are the common forms of modified starch used in the preparation of wound dressing. Bursali *et al.*, 2011 [472,183] prepared antimicrobial hydrogel films using potato starch-PVA complexed with boron using glutaraldehyde as a cross-linker. These hydrogels exhibited moderate antimicrobial activity (*in vitro*) against the tested bacterial and fungal strains, *E. coli* (14mm ZOI), *S. aureus* (13mm ZOI), *Pseudomonas aeruginosa* (*P. aeruginosa*) (12mm ZOI) and *Candida albicans* (*C. albicans*) (14mm ZOI) thus their potential wound management application could be further evaluated.

Kenawy *et al.*, 2014 [859,3] synthesised biodegradable hydrogel membranes for wound dressing purposes using HES, PVA and ampicillin. Physical crosslinking between HES and PVA was achieved by consecutive (three) freeze-thaw cycles. Use of HES in these hydrogels enhanced the swelling ability, capability of protein (BSA) adsorption and thermal stability of the formulation. The release (*in vitro*) of ampicillin in phosphate buffer at 37°C (pH 7.5) from the hydrogel formulation increased with an increase in HES content (0-75%). These hydrogel membranes exhibited improved physicochemical, mechanical, thermal, degradation and drug release properties, attributed to the addition of HES to PVA and have a potential in wound management applications.

Timmons *et al.*, 2008 [473,184], reported the effect of Aquaform<sup>®</sup> hydrogel dressing, (a modified starch copolymer with glycerol by Aspen Medical Europe Ltd) on the patient who developed moderate excoriation of the peri-anal area and multiple

Comment [GA25]: Kenawy *et al.*, 2014

superficial breaks around the anal and vulval region due to the faecal management system to deal with faecal incontinence. They found that Aquaform hydrogel therapy reduced pain and inflammation and prevented cutaneous infection resulting in complete healing of all the wounds. Askina<sup>®</sup> Gel (B.Braun Medical Ltd.); Flexigran (A1 Pharmaceuticals) and Iodosorb<sup>®</sup>, a Cadexomer iodine wound dressing (smith&nephew) are other commonly used starch based proprietary hydrogel dressings.

#### 4.9. Bacterial Cellulose (BC):

BC, a biosynthetic cellulose is produced by several bacteria (Rhizobium, Agrobacterium, Alcaligenes etc.) but *Gluconacetobacter xylinus*, a Gram negative rod shaped obligate aerobe, is the best known source for BC production [174, 175, 185, 186]. BC being hydrophilic, highly pure, biocompatible, nonpyrogenic [187, 176, 177, 178, 188, 189, 190] and transparent material has resulted in its use for fabrication of proprietary (XCell<sup>®</sup>, Bioprocess<sup>®</sup>, Dermafill<sup>™</sup>, Gengiflex<sup>®</sup> and Biofill<sup>®</sup>) wound dressings with the clinical rationale being to facilitate autolytic debridement. Portal *et al.*, (2009) [179, 191] published their findings of a sequential paired comparison of the rate of healing (75% reduction in wound size set as a primary outcome) during treatment of chronic non-healing lower extremity ulcers with standard dressings (gauze, foams and alginates) and commercially available BC dressing, Dermafill<sup>™</sup>. Wounds were initially treated with standard dressings and only the ones that failed to heal following 60 days or more were selected to be treated with BC dressing. The authors reported a significant improvement in chronic wounds,

Comment [GA26]: Gupta et al., 2017

achieving the primary outcome, with the use of Dermafill™ dressings, in a shorter period of time confirming that BC hydrogel dressings enhances wound healing.

Being interwoven nanofibrillar network structure, BC allows encapsulation of small molecules and this property has attracted vast research interest of loading different molecules in BC to tailor the properties of BC wound dressing [180,181,182,183,192,193,194,195]. Gupta *et al.*, (2016) [3] reported the synthesis of broad spectrum antibacterial BC hydrogel. Whilst not antimicrobial itself, BC was loaded with two forms of silver (Ag): silver nitrate (AgNO<sub>3</sub>) and silver zeolites (AgZ). The authors reported prolonged *in vitro* antibacterial activity (*S. aureus* and *P. aeruginosa*) with BC-AgZ formulation attributed to the double control system: first layer of control of Ag<sup>+</sup> release from zeolite cage structure and a second layer of controlled release by the BC hydrogel itself. Contrary to this, BC-AgNO<sub>3</sub> formulation, release of Ag<sup>+</sup> was only controlled by the BC matrix, hence less prolonged. Moreover, authors reported that the controlled release properties of the BC-AgZ hydrogel formulation minimises the toxicity associated with high topical Ag content.

#### **4.10. Carboxymethyl cellulose (CMC):**

CMC is a semi-synthetic, water-soluble ether derivative of cellulose in which H atoms from the hydroxyl groups are replaced with carboxymethyl [184,196]. CMC can be crosslinked to make biocompatible and biodegradable hydrogel with high water uptake capacity [65,185,197]. Its unique properties resulted in its use in proprietary hydrogel dressing products like FlexiGel™ and Regranex® gel (Smith & Nephew, UK) and Purilon Gel®, a sodium carboxymethyl cellulose (NaCMC) based hydrogel dressing (Coloplast).

Namazi *et al.*, (2016) [186198] fabricated a novel antibiotic loaded NaCMC/mesoporous silica nanoparticles [Mobile Composition of Matter No. 41 (MCM-41)] nanocomposite hydrogel with controlled release properties using citric acid as a crosslinker and glycerol as a plasticizer. Tetracycline was used as a broad spectrum antibiotic and methylene blue (cationic dye) were tested as antibacterial agents. The results suggested that MCM-41 in the NaCMC hydrogel enhanced the swelling properties and permeability of the formulation. With an increase of MCM-41 from 0-15%, the swelling ration doubled; water vapour and oxygen permeability increased dramatically. In another study, Rakhshaei and Namazi, (2017) [185197] synthesised a tetracycline-eluting nanocomposite bioactive hydrogel dressing using NaCMC/MCM-41 impregnated with zinc oxide (ZnO) as an antibacterial agent. Their findings suggest ZnO impregnation in MCM-41 enhanced the tetracycline (TC) loading due to the positive charge of ZnO nanoparticles attracting TC molecules (negative charge above pH 7.4) to the MCM-41 surface. Also, the release of TC improved from burst release in pure NaCMC films within the first 3 hours to sustained release with CMC/ZnO-MCM-41 nanocomposite hydrogel. The final formulation exhibited strong antimicrobial activity (in vitro) against *E. coli* and *S. aureus* due to combined antimicrobial activity of ZnO (antibacterial) and prolonged release of TC (antibiotic), supporting the potential use of this cytocompatible hydrogel formulation in wound management.

Comment [GA27]: Rakhshaei and Namazi, (2017)

Oliveira *et al.*, 2017 [187199] fabricated PVA-sodium carboxy methyl cellulose (NaCMC) hydrogel containing Propolis, a resinous bees product known for its wound healing and antimicrobial properties, by freeze-thaw technique. The hydrogel dressing designed for second degree burns offered added mechanical and swelling properties of PVA with flexibility and high water uptake properties of NaCMC. PVA-

NaCMC hydrogel with >15% propolis was proposed to be effective for wound healing as increased quantities of propolis lead to inferior mechanical properties.

#### 4.11. Poly (gamma glutamic acid) (PGGA):

PGGA is a bacterial derived natural anionic polymer of D- and L-glutamic acid with hydrophilic properties [200]. Due to its biocompatibility, non-toxic and biodegradable properties, it has attained a good prospect in the biomedical field including wound management applications. Although PGGA hydrogels have poor mechanical strength but this challenge can be encountered by using other polymers to tailor the physicochemical properties for wound dressing applications [200,201].

Comment [GA28]: Omowumi et al., 2014

Comment [GA29]: Khalil et al., 2017,

Shi et al., 2015 [202] fabricated biocompatible PGGA wound dressing hydrogels mixed with different weight ratio (0 (H-0), 5 (H-0.5), 10 (H-1) and 20(H-2) mmol) of silk sericin (biocompatible protein). Weight ratio of PGGA was kept constant (10mmol) in all hydrogels. Ethylene glycol diglycidyl ether (EGDGE) was used as a crosslinker in the production of hydrogels. The resulting hydrogels were easy to remove without damaging the healing tissue and demonstrated high swelling ratio with fluid absorption potential (mimicking wound exudate) which increased with the increase in the amount of silk serine. Moreover, cell proliferation study (by inverted light microscopy) confirmed that the addition of silk serine in PGGA hydrogels improved not only cell attachment but also its proliferation (L929) on the hydrogels. In addition, *in vivo* (rat model) experiments demonstrated that wound closure was accelerated in animals treated with PGGA based hydrogels (maximum closure in H-2) compared to the control (gauze). All these finding along with the histological results (significant granulation and capillary formation in wounds treated with H-2 on day 9) support the application of these novel hydrogel as wound dressing.

In another study, Zhang *et al.*, 2018 [203] described a procedure of producing composite hydrogels of PGGA with chitosan and heparin (Chitosan/Hep/PGGA ratio 10:5:5) as wound dressing for chronic wounds. Chitosan (polycation) when mixed with heparin (Hep) and PGGA (polyanions) in the presence of acetic acid, lead to the formation of hydrogels resulting from electrostatic interactions from oppositely charged agents. These hydrogels were loaded with superoxide dismutase (SOD) which imparted anti-oxidant properties. *In vivo* study (diabetic rat model) demonstrated accelerated wound closure (re-epithelialisation) in test group [Chitosan/Hep/PGGA (89.8±2.8%) and SOD-Chitosan/Hep/PGGA (92.0±3.7%)] compared to the control [3M wound dressing and gauze (85.4±2.4%)]. Collagen deposition findings (Masson's trichrome staining) were consistent with the results of wound closure study. Therefore authors concluded that SOD-loaded PGGA composite hydrogels hold a good prospect as wound dressings due to their collagen deposition and re-epithelialisation properties.

**Table 3.** Other natural and synthetic polymeric material used individually or in combination with other polymers for the production of hydrogel wound dressings.

	Source	Properties	Model/Case Study	Results	Commercial products	References
<b>Collagen</b>	Bovine; Porcine; Avian Rodent Marine	Natural polymer, nontoxic, biocompatible, biodegradable, haemostatic, support fibroblast growth, creates wound healing environment, stimulate macrophages and fibroblast, promote cell attachment and proliferation, cellular migration and tissue development.	Wounds in diabetic mice [Moura et al., 2014]  Burn wounds in male rats [Oryan et al., 2018]	Promotes wound healing and epithelialisation	Woun'Dres <sup>®</sup> (Coloplast)  Regenecare <sup>®</sup> (MPM Medical Inc.)	<a href="#">204,205,206,207,208,188</a> <a href="#">189</a> <a href="#">190</a> <a href="#">191</a> <a href="#">192</a>
<b>Gelatin</b>	Partial denaturation of bovine or porcine collagen	Natural polymer, Type A and B gelatine, elastic, biocompatible, biodegradable, activate microphages, haemostatic, high water absorption capacity, forms thermally-reversible hydrogels	Wounds in diabetic mice [Yoon et al., 2016]	Chemokine-loaded gelatin hydrogel dressings promoted healing, enhanced re-epithelialisation, neovascularisation	HyStem <sup>®</sup> -C (BioTime Inc.)  Extracel-HP <sup>™</sup> (Glycosan Biosystems)	<a href="#">172,209,210,211,212,213,164</a> <a href="#">193</a> <a href="#">194</a> <a href="#">195</a> <a href="#">196</a> <a href="#">197</a>
<b>Hyaluronic acid</b>	Bacterial fermentation;  Extraction from animal tissues	Poly anionic biological macromolecule, biocompatible, biodegradable, non-immunogenic, non-thrombogenic, hydrophilic, antioxidant activity by reacting with oxygen-derived free radicals, wound healing activity by stimulating inflammatory signals and facilitate cell motility and proliferation.	Wounds in diabetic mice [da Silva et al., 2017]	HA hydrogels accelerated wound closure and wound healing. When incorporated with stem cells increased neoepidermis thickness observed	Restore <sup>®</sup> Hydrogels (Hollister woundcare)  Regenecare <sup>®</sup> HA  HyStem <sup>™</sup> (BioTime Inc.)	<a href="#">214,215,216,217</a> <a href="#">198</a> <a href="#">199</a> <a href="#">200</a> <a href="#">201</a>
<b>Dextran</b>	<i>Leuconostoc spp</i> <i>Weissella spp</i> <i>Lactobacilli</i>	Bacterial polysaccharide, biocompatible, biodegradable, hydrophilic, stimulate wound healing, enhance angiogenesis, promote reepithelialisation	Burn wounds in mice [Sun et al., 2011]  Wounds in mice [Alibolandi et al., 2017]	Promotes wound healing, enables neovascularisation, promotes angiogenesis, accelerates epithelial maturation, dermal differentiation and skin regeneration Dextran hydrogels		<a href="#">131,218,219,220,221,222</a> <a href="#">120</a> <a href="#">202</a> <a href="#">203</a> <a href="#">204</a> <a href="#">205</a> <a href="#">206</a>

				accelerate wound healing which was further improved by loading hydrogels with curcumin nanomicelles		
<b>Glucan</b>	Cell wall of bacteria, yeasts, algae, lichens, plants (oats and barley)	Polysaccharide, biocompatible, biodegradable, antibacterial, antiviral, anti-inflammatory, exhibits wound healing activity, immune enhancing ability, enhances tensile strength of scar tissue,	26 patients (human subjects) with Hard-to-heal wounds like leg ulcers, diabetic foot ulcers and pressure ulcers [King <i>et al.</i> , 2017] Wounds in diabetic mice [Grip <i>et al.</i> , 2018]	Beta-glucan based Woulgan was very easy to apply and remove, capable of restarting healing process in a range of stalled wounds with wound size reduction	Woulgan® [Biotec Betaglucans]	<a href="#">223,224,225,226</a> <a href="#">207</a> <a href="#">208</a> <a href="#">209</a> <a href="#">210</a>
<b>Guar Gum</b>	<i>Cyamopsis tetragonolobus</i>	High molecular weight non-ionic natural hetero-polysaccharide, low cost, hydrophilic, nontoxic, biodegradable, biocompatible, FDA approved			ActivHeal® (Advanced Medical Solutions Ltd.)  3M™ Tegaderm™ Hydrogel Wound Filler (3M Health Care)	<a href="#">70,227,228,229</a> <a href="#">211</a> <a href="#">212</a> <a href="#">213</a>
<b>Polyurethanes</b>	Synthetic polymers with repetitive urethane groups produced by condensation and	Biocompatible, nontoxic, good strength, good toughness, tear resistance, abrasion resistance, non-allergenic, favours epithelialisation, allows oxygen permeability	81 patients (human subjects) with acute and chronic wounds [Zoellner <i>et</i>	Enhanced granulation and epithelialisation, reduction in wound surface slough, pain relief, wound size reduction	Hydrosorb® (Hartmann) Hydrosorb® Comfort (Hartmann)	<a href="#">230,231,232</a> <a href="#">214</a> <a href="#">215</a> <a href="#">216</a>

	polymerisation methods		<i>al.</i> , 2007] Wounds in rat model [Bankoti et al., 2017]	Enhanced wound healing, increased neovascularization; higher re-epithelialisation, increased collagen synthesis	
<b>Poly(acrylic acid)</b>	Synthetic polymer produced by polymerisation of acrylic acid	Biocompatible, biodegradable, hydrophilic, pH responsive polymer so can be utilised in producing smart hydrogels, anti-bacterial	Wounds in Swiss mice [Champeau et al., 2018]	Nitric oxide controlled release PAA hydrogels lead to increased angiogenesis, organised collagen and accelerated wound contraction	<a href="#">233,234,235</a> <a href="#">247</a> <a href="#">248</a> <a href="#">249</a>
<b>2-acrylamido-2-methylpropane sulfonic acid (AMPS)</b>	Commercially available or by Ritter reaction of acrylonitrile-isobutylene with sulphuric acid	Hydrophilic, non-toxic, biocompatible, thermal stability, pH independent swelling stability, good coherency with good skin adhesion, easy to remove from wound surface, high oxygen permeability, flexible	Porcine burn model [Boonkaew et al., 2014a]	Silver nanoparticle loaded AMPS hydrogels efficiently prevented bacterial colonisation of wound during healing process	<a href="#">117</a> <a href="#">122</a> <a href="#">236</a> <a href="#">237</a> <a href="#">238</a> <a href="#">110</a> <a href="#">115</a> <a href="#">220</a> <a href="#">221</a> <a href="#">222</a>

**Comment [GA30]:** Witthayapra..2012

**Comment [GA31]:** Wang 2007

## 5. Conclusion and further perspectives

Chronic wounds impose an immense socio-economic burden and if fail to respond to the available medical interventions, may lead to amputation, leading to severe physical trauma and emotional distress to patients and their families. Chronic non-healing wounds may take several months to heal leading to multi-fold financial expenditure on management compared to acute wounds. Although there is a plethora of proprietary wound dressing products already available in the market but due to the increase in ageing population and incidences of chronic diseases, there is a critical need to continue to develop improved advanced wound dressings. Advanced wound care that hydrogel dressings form part of, make up around \$7.1 billion of the wound care market and to match the increasing treatment needs in this sector, it is growing at an annual rate of 8.3%. This review presents a brief description of wound healing process and current state of wound dressing products with the main emphasis on hydrogels as wound dressings. Hydrogels, due to their unique properties, are considered as one of the most promising candidates for wound management as dressings. Non-toxicity, biocompatibility, biodegradability, high water content, moisture-retentive property, soft texture, swelling and de-swelling behaviour, stimuli-responsive potential, interactive nature, controlled delivery of therapeutic agents and low cost are few of the many unique properties of hydrogel dressings. These dressings can be fabricated using several polymeric materials by variety of physical and chemical cross-linking techniques. Presented review also expands its focus on the material aspect of the natural and synthetic polymers used in hydrogel formation. From the evidence based on clinical case studies of the application of proprietary hydrogel dressing products in acute and chronic wound management; *in vitro* studies and *in vivo* biological models for testing new hydrogel

material with potential clinical applications, it can be concluded that hydrogels are one of the ideal candidates for wound management as dressing material. Further research progress leading to low cost proprietary hydrogel dressings to facilitate and accelerate chronic wound healing should be the focus for the future in the area of wound care.

**Comment [GA32]:** Kindly elaborate this section as recommended by Reviewer 2.

### **Acknowledgement**

AG acknowledges the University of Wolverhampton for supporting his doctoral studies. Thanks to Brian Johnston for his kind assistance in designing images for the manuscript.

## References

1. S.K. Han, Basics of Wound Healing, second ed., in: Innovations and Advances in Wound Healing, Springer, Berlin, 2016, pp.1–37. doi:10.1007/978-3-662-46587-5\_1.
2. M. Martin, Physiology of Wound Healing, in: Flanagan (Ed.), Wound Healing and Skin Integrity: Principles and Practice, John Wiley & Sons, Ltd., U.K., 2013, pp. 33-51.
3. A. Gupta, W.L. Low, I. Radecka, S.T. Britland, M. Mohd Amin Cairul Iqbal, C. Martin, Characterisation and in vitro antimicrobial activity of biosynthetic silver-loaded bacterial cellulose hydrogels, *J. Microencapsul.* 33 (2016) 725–734. doi:10.1080/02652048.2016.1253796.
4. S. Saghazadeh, C. Rinoldi, M. Schot, S.S. Kashaf, F. Sharifi, E. Jalilian, K. Nuutila, G. Giatsidis, P. Mostafalu, H. Derakhshandeh, K. Yue, W. Swieszkowski, A. Memic, A. Tamayol, A. Khademhosseini, Drug delivery systems and materials for wound healing applications, *Adv. Drug Deliv. Rev.* 127 (2018) 138–166. doi:10.1016/j.addr.2018.04.008.
5. M. Flanagan, Wound Healing and Skin Integrity: Principles and Practice, first ed., Wiley-Blackwell, UK, 2013.
6. C. Martin, W.L. Low, M.C.I.M. Amin, I. Radecka, P. Raj, K. Kenward, Current trends in the development of wound dressings, biomaterials and devices, *Pharm. Pat. Anal.* 2 (2013) 341–359. doi:10.4155/ppa.13.18.
7. S. Tejiram, S.L. Kavalukas, J.W. Shupp, A. Barbul, Fundamentals and strategies for wound healing, in: M. Agren (Ed.), Wound Healing Biomaterials-Volume 1: Therapies and Reeneration, WP Woodhead Publishing, U.K., 2016, pp. 3–39. doi:10.1016/b978-1-78242-455-0.00001-x.
8. C. Dealey, The Physiology of Wound Healing, in: the care of wounds: A Guide for Nurses, Wiley-Blackwell, U.K., 2012, pp. 1–14. doi:10.1002/9780470774946.ch1.
9. W. Paul, C.P. Sharma, The Role of Growth Factors, Cytokines, Nutrition and Matrix Metalloproteinases, in Wound Healing, in: Advances in Wound Healing Materials: Science and Skin Engineering, Smithers Group Company, Shropshire, U.K., 2015, pp. 61-80.
10. P.H. Wang, B.S. Huang, H.C. Horng, C.C. Yeh, Y.J. Chen, Wound healing, *J. Chinese Medical Assoc.* 81 (2018) 94-101. doi.org/10.1016/j.jcma.2017.11.002.
11. T. Lucas, A. Waisman, R. Ranjan, J. Roes, T. Krieg, W. Muller, A. Roers, S.A. Eming, Differential Roles of Macrophages in Diverse Phases of Skin Repair, *J. Immunol.* 184 (2010) 3964–3977. doi:10.4049/jimmunol.0903356.
12. S.D. Tymen, I.G. Rojas, X. Zhou, Z.J. Fang, Y. Zhao, P.T. Marucha, Restraint stress alters neutrophil and macrophage phenotypes during wound healing, *Brain. Behav. Immun.* 28 (2013) 207–217. doi:10.1016/j.bbi.2012.07.013.

13. T. Velnar, T. Bailey, V. Smrkolj, The Wound Healing Process: An Overview of the Cellular and Molecular Mechanisms, *J. Int. Med. Res.* 37 (2009) 1528–1542. doi:10.1177/147323000903700531.
14. S. Singh, A. Young, C.-E. McNaught, The physiology of wound healing, *Surg.* 35 (2017) 473–477. doi:10.1016/j.mpsur.2017.06.004.
15. C. Qing, The molecular biology in wound healing & non-healing wound, *Chinese J. Traumatol.* 20 (2017) 189–193. doi:10.1016/j.cjtee.2017.06.001.
16. T.J. Koh, L.A. DiPietro, Inflammation and wound healing: the role of the macrophage, *Expert Rev. Mol. Med.* 13 (2011). doi:10.1017/s1462399411001943.
17. L. Häkkinen, L. Koivisto, J. Heino, H. Larjava, Cell and Molecular Biology of Wound Healing, in: A. Vishwakarma, P. Sharpe, S. Shi, M. Ramalingam (Eds.), *Stem Cell Biology and Tissue Engineering in Dental Sciences*, Academic Press, U.K., 2015, pp. 669–690. doi:10.1016/b978-0-12-397157-9.00054-0.
18. A. Kasuya, Y. Tokura, Attempts to accelerate wound healing, *J. Dermatol. Sci.* 76 (2014) 169–172. doi:10.1016/j.jdermsci.2014.11.001.
19. J. Koehler, F.P. Brandl, A.M. Goepferich, Hydrogel wound dressings for bioactive treatment of acute and chronic wounds, *Eur. Polym. J.* 100 (2018) 1–11. doi:10.1016/j.eurpolymj.2017.12.046.
20. L.M. Morton, T.J. Phillips, Wound healing and treating wounds, *J. Am. Acad. Dermatol.* 74 (2016) 589–605. doi:10.1016/j.jaad.2015.08.068.
21. S. Schreml, R.-M. Szeimies, L. Prantl, M. Landthaler, P. Babilas, Wound healing in the 21st century, *J. Am. Acad. Dermatol.* 63 (2010) 866–881. doi:10.1016/j.jaad.2009.10.048.
22. D. Kiritsi, A. Nyström, The role of TGF $\beta$  in wound healing pathologies, *Mech. Ageing Dev.* 172 (2018) 51–58. doi:10.1016/j.mad.2017.11.004.
23. S. Guo, L.A. DiPietro, Factors Affecting Wound Healing, *J. Dent. Res.* 89 (2010) 219–229. doi:10.1177/0022034509359125.
24. J.F. Guest, N. Ayoub, T. McIlwraith, I. Uchegbu, A. Gerrish, D. Weidlich, K. Vowden, P. Vowden, Health economic burden that different wound types impose on the UK's National Health Service, *Int. Wound J.* 14 (2017) 322–330. doi: 10.1111/iwj.12603.
25. P. Krzyszczyk, R. Schloss, A. Palmer, F. Berthiaume, The Role of Macrophages in Acute and Chronic Wound Healing and Interventions to Promote Pro-wound Healing Phenotypes, *Frontiers in physiology.* 9 (2018). doi: 10.3389/fphys.2018.00419.
26. S. Barrientos, O. Stojadinovic, M.S. Golinko, H. Brem, M. Tomic-Canic, PERSPECTIVE ARTICLE: Growth factors and cytokines in wound healing, *Wound Repair Regen.* 16 (2008) 585–601. doi:10.1111/j.1524-475x.2008.00410.x.
27. G.S. Schultz, A. Wysocki, Interactions between extracellular matrix and growth factors in wound healing, *Wound Repair Regen.* 17 (2009) 153–162. doi:10.1111/j.1524-475x.2009.00466.x.

28. D.H. Yang, D.I. Seo, D.-W. Lee, S.H. Bhang, K. Park, G. Jang, C.H. Kim, H.J. Chun, Preparation and evaluation of visible-light cured glycol chitosan hydrogel dressing containing dual growth factors for accelerated wound healing, *J. Ind. Eng. Chem.* 53 (2017) 360–370. doi:10.1016/j.jiec.2017.05.007.
29. Q. Li, Y. Niu, H. Diao, L. Wang, X. Chen, Y. Wang, L. Dong, C. Wang, In situ sequestration of endogenous PDGF-BB with an ECM-mimetic sponge for accelerated wound healing, *Biomaterials.* 148 (2017) 54–68. doi:10.1016/j.biomaterials.2017.09.028.
30. Z. Xie, C.B. Paras, H. Weng, P. Punnakitkashem, L.-C. Su, K. Vu, L. Tang, J. Yang, K.T. Nguyen, Dual growth factor releasing multi-functional nanofibers for wound healing, *Acta Biomater.* 9 (2013) 9351–9359. doi:10.1016/j.actbio.2013.07.030.
31. Y. Yoo, H. Hyun, S.-J. Yoon, S.Y. Kim, D.-W. Lee, S. Um, S.O. Hong, D.H. Yang, Visible light-cured glycol chitosan hydrogel dressing containing endothelial growth factor and basic fibroblast growth factor accelerates wound healing in vivo, *J. Ind. Eng. Chem.* (2018). ***In Press.*** doi:10.1016/j.jiec.2018.07.009.
32. E. João De Masi Carolina David, A.C.L. Campos, D.M. João, M.A.S. Ratti, I.S. Ike, D.M. João, The influence of growth factors on skin wound healing in rats, *Braz. J. Otorhinolaryngol.* 82 (2016) 512–521. doi:10.1016/j.bjorl.2015.09.011.
33. J. Devalliere, K. Dooley, Y. Hu, S.S. Kelangi, B.E. Uygun, M.L. Yarmush, Co-delivery of a growth factor and a tissue-protective molecule using elastin biopolymers accelerates wound healing in diabetic mice, *Biomaterials.* 141 (2017) 149–160. doi:10.1016/j.biomaterials.2017.06.043.
34. J. Yang, W. Qiang, S. Ren, S. Yi, J. Li, L. Guan, L. Du, Y. Guo, H. Hu, H. Li, X. Li, High-efficiency production of bioactive oleosin-basic fibroblast growth factor in *A. thaliana* and evaluation of wound healing, *Gene.* 639 (2018) 69–76. doi:10.1016/j.gene.2017.09.064.
35. G. Ramanathan, T. Muthukumar, U. Tirichurapalli Sivagnanam, In vivo efficiency of the collagen coated nanofibrous scaffold and their effect on growth factors and pro-inflammatory cytokines in wound healing, *Eur. J. Pharmacol.* 814 (2017) 45–55. doi:10.1016/j.ejphar.2017.08.003.
36. I. Garcia-Orue, G. Gainza, F.B. Gutierrez, J.J. Aguirre, C. Evora, J.L. Pedraz, R.M. Hernandez, A. Delgado, M. Igartua, Novel nanofibrous dressings containing rhEGF and Aloe vera for wound healing applications, *Int. J. Pharm.* 523 (2017) 556–566. doi:10.1016/j.ijpharm.2016.11.006.
37. K.H. Park, S.H. Han, J.P. Hong, S.-K. Han, D.-H. Lee, B.S. Kim, J.H. Ahn, J.W. Lee, Topical epidermal growth factor spray for the treatment of chronic diabetic foot ulcers: A phase III multicenter, double-blind, randomized, placebo-controlled trial, *Diabetes Res. Clin. Pract.* 142 (2018) 335–344. doi:10.1016/j.diabres.2018.06.002.
38. M.S. Lord, A.L. Ellis, B.L. Farrugia, J.M. Whitelock, H. Grenett, C. Li, R.L. O'Grady, A.A. DeCarlo, Perlecan and vascular endothelial growth factor-

- encoding DNA-loaded chitosan scaffolds promote angiogenesis and wound healing, *J. Control. Release.* 250 (2017) 48–61. doi:10.1016/j.jconrel.2017.02.009.
39. M. Ram, V. Singh, S. Kumawat, D. Kumar, M.C. Lingaraju, T. Uttam Singh, A. Rahal, S. Kumar Tandan, D. Kumar, Deferoxamine modulates cytokines and growth factors to accelerate cutaneous wound healing in diabetic rats, *Eur. J. Pharmacol.* 764 (2015) 9–21. doi:10.1016/j.ejphar.2015.06.029.
40. J. Ding, P. Kwan, Z. Ma, T. Iwashina, J. Wang, H.A. Shankowsky, E.E. Tredget, Synergistic effect of vitamin D and low concentration of transforming growth factor beta 1, a potential role in dermal wound healing, *Burns.* 42 (2016) 1277–1286. doi:10.1016/j.burns.2016.03.009.
41. B. Behm, P. Babilas, M. Landthaler, S. Schreml, Cytokines, chemokines and growth factors in wound healing, *J. Eur. Acad. Dermatology Venereol.* 26 (2012) 812–820. doi:10.1111/j.1468-3083.2011.04415.x.
42. L. Zhang, T. Berta, Z.-Z. Xu, T. Liu, J.Y. Park, R.-R. Ji, TNF- $\alpha$  contributes to spinal cord synaptic plasticity and inflammatory pain: Distinct role of TNF receptor subtypes 1 and 2, *Pain.* 152 (2011) 419–427. doi:10.1016/j.pain.2010.11.014.
43. L.I.F. Moura, A.M.A. Dias, E. Carvalho, H.C. de Sousa, Recent advances on the development of wound dressings for diabetic foot ulcer treatment—A review, *Acta Biomater.* 9 (2013) 7093–7114. doi:10.1016/j.actbio.2013.03.033.
44. C. Daunton, S. Kothari, L. Smith, D. Steele, A history of materials and practices for wound management. *Wound Practice and Research*, **20** (2012) 174-186.
45. A.A. Arroyo, P.L. Casanova, J.V. Soriano, i. B. Torra, Open-label clinical trial comparing the clinical and economic effectiveness of using a polyurethane film surgical dressing with gauze surgical dressings in the care of post-operative surgical wounds, *Int. Wound J.* 12 (2015) 285–292. doi:10.1111/iwj.12099.
46. R. Jayakumar, M. Prabakaran, P.T. Sudheesh Kumar, S. V Nair, H. Tamura, Biomaterials based on chitin and chitosan in wound dressing applications, *Biotechnol. Adv.* 29 (2011) 322–337. doi:10.1016/j.biotechadv.2011.01.005.
47. H.F. Selig, D.B. Lumenta, M. Giretzlehner, M.G. Jeschke, D. Upton, L.P. Kamolz, The properties of an “ideal” burn wound dressing – What do we need in daily clinical practice? Results of a worldwide online survey among burn care specialists, *Burns.* 38 (2012) 960–966. doi:10.1016/j.burns.2012.04.007.
48. S.-H. Chen, C.-T. Tsao, C.-H. Chang, Y.-T. Lai, M.-F. Wu, C.-N. Chuang, H.-C. Chou, C.-K. Wang, K.-H. Hsieh, Assessment of reinforced poly(ethylene glycol) chitosan hydrogels as dressings in a mouse skin wound defect model, *Mater. Sci. Eng. C.* 33 (2013) 2584–2594. doi:10.1016/j.msec.2013.02.031.
49. P.I. Morgado, P.F. Lisboa, M.P. Ribeiro, S. Miguel, P.C. Simões, I.J. Correia, A. Aguiar-Ricardo, Poly(vinyl alcohol)/chitosan asymmetrical membranes: Highly controlled morphology toward the ideal wound dressing, *J. Memb. Sci.* 469 (2014) 262–271. doi:10.1016/j.memsci.2014.06.035.

50. K. Vowden, P. Vowden, Wound dressings: principles and practice, *Surg.* 35 (2017) 489–494. doi:10.1016/j.mpsur.2017.06.005.
51. V. Andreu, G. Mendoza, M. Arruebo, S. Irusta, Smart Dressings Based on Nanostructured Fibers Containing Natural Origin Antimicrobial, Anti-Inflammatory, and Regenerative Compounds, *Materials (Basel)*. 8 (2015) 5154–5193. doi:10.3390/ma8085154.
52. G.D. Winter, Formation of the Scab and the Rate of Epithelization of Superficial Wounds in the Skin of the Young Domestic Pig, *Nature*. 193 (1962) 293–294. doi:10.1038/193293a0.
53. M. Kokabi, M. Sirousazar, Z.M. Hassan, PVA–clay nanocomposite hydrogels for wound dressing, *Eur. Polym. J.* 43 (2007) 773–781. doi:10.1016/j.eurpolymj.2006.11.030.
54. C. Dealey, General Principles of Wound Management, in: *the care of wounds: A Guide for Nurses*, Wiley-Blackwell, U.K., 2012, pp. 61–91. doi:10.1002/9780470774946.ch1.
55. F.T. Martin, J.B. O'Sullivan, P.J. Regan, J. McCann, J.L. Kelly, Hydrocolloid dressing in pediatric burns may decrease operative intervention rates, *J. Pediatr. Surg.* 45 (2010) 600–605. doi:10.1016/j.jpedsurg.2009.09.037.
56. K. Skórkowska-Telichowska, M. Czemplik, A. Kulma, J. Szopa, The local treatment and available dressings designed for chronic wounds, *J. Am. Acad. Dermatol.* 68 (2013) e117–e126. doi:10.1016/j.jaad.2011.06.028.
57. F.E. Brölmann, A.M. Eskes, J.C. Goslings, F.B. Niessen, R. de Bree, A.C. Vahl, E.G. Pierik, H. Vermeulen, D.T. Ubbink, Randomized clinical trial of donor-site wound dressings after split-skin grafting, *Br. J. Surg.* 100 (2013) 619–627. doi:10.1002/bjs.9045.
58. J.G. Powers, L.M. Morton, T.J. Phillips, Dressings for chronic wounds, *Dermatol. Ther.* 26 (2013) 197–206. doi:10.1111/dth.12055.
59. N. Santamaria, M. Gerdtz, S. Sage, J. McCann, A. Freeman, T. Vassiliou, S. De Vincentis, A.W. Ng, E. Manias, W. Liu, J. Knott, A randomised controlled trial of the effectiveness of soft silicone multi-layered foam dressings in the prevention of sacral and heel pressure ulcers in trauma and critically ill patients: the border trial, *Int. Wound J.* 12 (2013) 302–308. doi:10.1111/iwj.12101.
60. E.-H. Song, S.-H. Jeong, J.-U. Park, S. Kim, H.-E. Kim, J. Song, Polyurethane-silica hybrid foams from a one-step foaming reaction, coupled with a sol-gel process, for enhanced wound healing, *Mater. Sci. Eng. C*. 79 (2017) 866–874. doi:10.1016/j.msec.2017.05.041.
61. J.G. Powers, C. Higham, K. Broussard, T.J. Phillips, Wound healing and treating wounds: Chronic wound care and management, *J. Am. Acad. Dermatol.* 74 (2016) 607–625. doi:10.1016/j.jaad.2015.08.070.
62. G. Cirillo, M. Curcio, U.G. Spizzirri, O. Vittorio, P. Tucci, N. Picci, F. Iemma, S. Hampel, F.P. Nicoletta, Carbon nanotubes hybrid hydrogels for electrically tunable release of Curcumin, *Eur. Polym. J.* 90 (2017) 1–12. doi:10.1016/j.eurpolymj.2017.03.011.

63. S. Tyeb, N. Kumar, A. Kumar, V. Verma, Flexible agar-sericin hydrogel film dressing for chronic wounds, *Carbohydr. Polym.* 200 (2018) 572–582. doi:10.1016/j.carbpol.2018.08.030.
64. S. Varghese, C. Jamora, Hydrogels: a versatile tool with a myriad of biomedical and research applications for the skin, *Expert Rev. Dermatol.* 7 (2012) 315–317. doi:10.1586/edm.12.28.
65. N. Capanema, A.A.P. Mansur, A.C. de Jesus, S.M. Carvalho, L.C. de Oliveira, H.S. Mansur, Superabsorbent crosslinked carboxymethyl cellulose-PEG hydrogels for potential wound dressing applications, *Int. J. Biol. Macromol.* 106 (2018) 1218–1234. doi:10.1016/j.ijbiomac.2017.08.124.
66. L. Fan, H. Yang, J. Yang, M. Peng, J. Hu, Preparation and characterization of chitosan/gelatin/PVA hydrogel for wound dressings, *Carbohydr. Polym.* 146 (2016) 427–434. doi:10.1016/j.carbpol.2016.03.002.
67. S.P. Miguel, M.P. Ribeiro, H. Brancal, P. Coutinho, I.J. Correia, Thermoresponsive chitosan–agarose hydrogel for skin regeneration, *Carbohydr. Polym.* 111 (2014) 366–373. doi:10.1016/j.carbpol.2014.04.093.
68. L. Zhu, K.M. Bratlie, pH sensitive methacrylated chitosan hydrogels with tunable physical and chemical properties, *Biochem. Eng. J.* 132 (2018) 38–46. doi:10.1016/j.bej.2017.12.012.
69. D. Mukherjee, M. Azamthulla, S. Santhosh, G. Dath, A. Ghosh, R. Natholia, J. Anbu, B. V Teja, K.M. Muzammil, Development and characterization of chitosan-based hydrogels as wound dressing materials, *J. Drug Deliv. Sci. Technol.* 46 (2018) 498–510. doi:10.1016/j.jddst.2018.06.008.
70. B.S. Kaith, R. Sharma, S. Kalia, Guar gum based biodegradable, antibacterial and electrically conductive hydrogels, *Int. J. Biol. Macromol.* 75 (2015) 266–275. doi:10.1016/j.ijbiomac.2015.01.046.
71. K. Pal, A.K. Banthia, D.K. Majumdar, Polymeric Hydrogels: Characterization and Biomedical Applications, *Des. Monomers Polym.* 12 (2009) 197–220. doi:10.1163/156855509x436030.
72. H. Li, J. Yang, X. Hu, J. Liang, Y. Fan, X. Zhang, Superabsorbent polysaccharide hydrogels based on pullulan derivate as antibacterial release wound dressing, *J. Biomed. Mater. Res. Part A.* 98A (2011) 31–39. doi:10.1002/jbm.a.33045.
73. E. Caló, V. V. Khutoryanskiy, Biomedical applications of hydrogels: A review of patents and commercial products, *Eur. Polym. J.* 65 (2015) 252–267. doi:10.1016/j.eurpolymj.2014.11.024.
74. D.Q. Wu, J. Zhu, H. Han, J.-Z. Zhang, F.-F. Wu, X.-H. Qin, J.-Y. Yu, Synthesis and characterization of arginine-NIPAAm hybrid hydrogel as wound dressing: In vitro and in vivo study, *Acta Biomater.* 65 (2018) 305–316. doi:10.1016/j.actbio.2017.08.048.
75. B. Singh, A. Dhiman, Designing bio-mimetic moxifloxacin loaded hydrogel wound dressing to improve antioxidant and pharmacology properties, *RSC Adv.* 5 (2015) 44666–44678. doi:10.1039/c5ra06857f.

76. J.S. Gonzalez, L.N. Ludueña, A. Ponce, V.A. Alvarez, Poly(vinyl alcohol)/cellulose nanowhiskers nanocomposite hydrogels for potential wound dressings, *Mater. Sci. Eng. C.* 34 (2014) 54–61. doi:10.1016/j.msec.2013.10.006.
77. M. Madaghiele, A. Sannino, L. Ambrosio, C. Demitri, Polymeric hydrogels for burn wound care: Advanced skin wound dressings and regenerative templates, *Burn. Trauma.* 2 (2014) 153-161. doi:10.4103/2321-3868.143616.
78. O. Guaresti, C. García-Astrain, R.H. Aguirresarobe, A. Eceiza, N. Gabilondo, Synthesis of stimuli-responsive chitosan-based hydrogels by Diels–Alder cross-linking ‘click’ reaction as potential carriers for drug administration, *Carbohydr. Polym.* 183 (2018) 278–286. doi:10.1016/j.carbpol.2017.12.034.
79. N. Sood, A. Bhardwaj, S. Mehta, A. Mehta, Stimuli-responsive hydrogels in drug delivery and tissue engineering, *Drug Deliv.* 23 (2016) 748-770. doi:10.3109/10717544.2014.940091.
80. Gupta, A., Kowalczyk, M., Martin, C., Radecka, I. ISBPPB 2018, Page 40 Biosynthetic Cellulose Based Hydrogels of Curcumin Encapsulated in Cyclodextrins as Wound Dressings. [https://isbppb2018.org/upload/isbppb2018/ISBPPB\\_2018\\_FINAL\\_PROGRAM\\_ME\\_AND\\_BOOK\\_OF\\_ABSTRACTS.pdf](https://isbppb2018.org/upload/isbppb2018/ISBPPB_2018_FINAL_PROGRAM_ME_AND_BOOK_OF_ABSTRACTS.pdf).
81. Sun Y, Du L, Liu Y, Li M, Li X, Jin Y, Qian X. Transdermal delivery of the in situ hydrogels of curcumin and its inclusion complexes of hydroxypropyl-β-cyclodextrin for melanoma treatment. International Journal of Pharmaceutics 2014;469(1):31-39.
82. Ramírez Barragán CA, Macías Balleza ER, García-Uriostegui L, Andrade Ortega JA, Toriz G, Delgado E. Rheological characterization of new thermosensitive hydrogels formed by chitosan, glycerophosphate, and phosphorylated β-cyclodextrin. Carbohydrate Polymers 2018;201:471-481.
83. Jaruporn Rakmai, Benjamas Cheirsilp, Ana Torrado-Agrasar, Jesús Simal-Gándara, Juan Carlos Mejuto. Encapsulation of yarrow essential oil in hydroxypropyl-beta-cyclodextrin: physicochemical characterization and evaluation of bio-efficacies. CYTA: Journal of Food 2017;15(3):409.
84. Jeong D, Joo S, Shinde VV, Jung S. Triple-crosslinked β-cyclodextrin oligomer self-healing hydrogel showing high mechanical strength, enhanced stability and pH responsiveness. Carbohydrate Polymers 2018;198:563-574.
85. Lee MS, Seo SR, Kim J-. A β-cyclodextrin, polyethyleneimine and silk fibroin hydrogel containing Centella asiatica extract and hydrocortisone acetate: releasing properties and in vivo efficacy for healing of pressure sores. Clinical and Experimental Dermatology 2012;37(7):762-771.
86. T.R. Hoare, D.S. Kohane, Hydrogels in drug delivery: Progress and challenges, Polymer. 49 (2008) 1993–2007. doi:10.1016/j.polymer.2008.01.027.

Formatted: Justified, Space After: 10 pt, Line spacing: Double, Pattern: Clear

Formatted: Font: (Default) Arial, 12 pt, Font color: Custom Color (RGB(83,86,90)), Pattern: Clear (White)

- 79-87. [Pinho E, Grootveld M, Soares G, Henriques M. Cyclodextrin-based hydrogels toward improved wound dressings. \*Critical Reviews in Biotechnology\* 2014;34\(4\):328-337.](#)
- 80-88. P. Aguiar, C. Amaral, A. Rodrigues, A.H. de Souza, A diabetic foot ulcer treated with hydrogel and hyperbaric oxygen therapy: a case study, *J. Wound Care*. 26 (2017) 692-695. doi: 10.12968/jowc.2017.26.11.692.
- 81-89. A. Fleck, P.F.G. Cabral, F.F.M. Vieira, D.A. Pinheiro, C.R. Pereira, W.C. Santos, T.B. Machado, *Punica granatum* L. Hydrogel for Wound Care Treatment: From Case Study to Phytomedicine Standardization, *Molecules*. 21 (2016) 1059. doi: 10.3390/molecules21081059.
- 82-90. D.R. Solway, M. Consalter, D.J. Levinson, Microbial cellulose wound dressing in the treatment of skin tears in the frail elderly, *Wounds*. 22 (2010) 17-19.
- 83-91. E.M. Ahmed, Hydrogel: Preparation, characterization, and applications: A review, *J. Adv. Res.* 6 (2015) 105–121. doi:10.1016/j.jare.2013.07.006.
- 84-92. N. Wathoni, K. Motoyama, T. Higashi, M. Okajima, T. Kaneko, H. Arima, Physically crosslinked-sacran hydrogel films for wound dressing application, *Int. J. Biol. Macromol.* 89 (2016) 465–470. doi:10.1016/j.ijbiomac.2016.05.006.
- 85-93. E.-R. Kenawy, E.A. Kamoun, M.S. Mohy Eldin, M. El-Meligy, Physically crosslinked poly(vinyl alcohol)-hydroxyethyl starch blend hydrogel membranes: Synthesis and characterization for biomedical applications, *Arab. J. Chem.* 7 (2014) 372–380. doi:10.1016/j.arabjc.2013.05.026.
- 86-94. F. Ullah, M.B.H. Othman, F. Javed, Z. Ahmad, H.M. Akil, Classification, processing and application of hydrogels: A review, *Mater. Sci. Eng. C*. 57 (2015) 414–433. doi:10.1016/j.msec.2015.07.053.
- 87-95. A. Chaturvedi, A.K. Bajpai, J. Bajpai, S. K.Singh, Evaluation of poly (vinyl alcohol) based cryogel–zinc oxide nanocomposites for possible applications as wound dressing materials, *Mater. Sci. Eng. C*. 65 (2016) 408–418. doi:10.1016/j.msec.2016.04.054.
- 88-96. W.E. Hennink, C.F. van Nostrum, Novel crosslinking methods to design hydrogels, *Adv. Drug Deliv. Rev.* 64 (2012) 223–236. doi:10.1016/j.addr.2012.09.009.
- 89-97. M. Rezvanian, N. Ahmad, M. Mohd Amin Cairul Iqbal, S.-F. Ng, Optimization, characterization, and in vitro assessment of alginate-pectin ionic cross-linked hydrogel film for wound dressing applications, *Int. J. Biol. Macromol.* 97 (2017) 131–140. doi:10.1016/j.ijbiomac.2016.12.079.
- 90-98. R. Pereira, A. Carvalho, D.C. Vaz, M.H. Gil, A. Mendes, P. Bártolo, Development of novel alginate based hydrogel films for wound healing applications, *Int. J. Biol. Macromol.* 52 (2013) 221–230. doi:10.1016/j.ijbiomac.2012.09.031.
- 91-99. J.L. Holloway, A.M. Lowman, G.R. Palmese, The role of crystallization and phase separation in the formation of physically cross-linked PVA hydrogels, *Soft Matter*. 9 (2013) 826–833. doi:10.1039/c2sm26763b.

Formatted: Left, Space After: 8.65 pt, Line spacing: single, Pattern: Clear (White)

Formatted: Font: (Default) Arial, 12 pt, Font color: Custom Color(RGB(83,86,90))

- ~~92-100.~~ A.S. Ahmed, U.K. Mandal, M. Taher, D. Susanti, J.M. Jaffri, PVA-PEG physically cross-linked hydrogel film as a wound dressing: experimental design and optimization, *Pharm. Dev. Technol.* (2017) 1–10. doi:10.1080/10837450.2017.1295067.
- ~~93-101.~~ H. Zhang, F. Zhang, J. Wu, Physically crosslinked hydrogels from polysaccharides prepared by freeze–thaw technique, *React. Funct. Polym.* 73 (2013) 923–928. doi:10.1016/j.reactfunctpolym.2012.12.014.
- ~~94-102.~~ E.A. Kamoun, E.-R.S. Kenawy, T.M. Tamer, M. El-Meligy, M.S. Mohy Eldin, Poly (vinyl alcohol)-alginate physically crosslinked hydrogel membranes for wound dressing applications: Characterization and bio-evaluation, *Arab. J. Chem.* 8 (2015) 38–47. doi:10.1016/j.arabjc.2013.12.003.
- ~~95-103.~~ S.K.H. Gulrez, S. Al-Assaf, G. O. Phillips, Hydrogels: Methods of Preparation, Characterisation and Applications, *Prog. Mol. Environ. Bioeng.* (2011). doi:10.5772/24553.
- ~~96-1.~~ ~~T.R. Hoare, D.S. Kohane, Hydrogels in drug delivery: Progress and challenges, *Polymer.* 49 (2008) 1993–2007. doi:10.1016/j.polymer.2008.01.027.~~
- ~~97-104.~~ L. Liu, Q. Gao, X. Lu, H. Zhou, In situ forming hydrogels based on chitosan for drug delivery and tissue regeneration, *Asian J. Pharm. Sci.* 11 (2016) 673–683. doi:10.1016/j.ajps.2016.07.001.
- ~~98-105.~~ E. Kaditi, G. Mountrichas, S. Pispas, Amphiphilic block copolymers by a combination of anionic polymerization and selective post-polymerization functionalization, *Eur. Polym. J.* 47 (2011) 415–434. doi:10.1016/j.eurpolymj.2010.09.012.
- ~~99-106.~~ Y.-C. Tsai, S. Li, S.-G. Hu, W.-C. Chang, U.-S. Jeng, S. Hsu, Synthesis of Thermoresponsive Amphiphilic Polyurethane Gel as a New Cell Printing Material near Body Temperature, *ACS Appl. Mater. Interfaces.* 7 (2015) 27613–27623. doi:10.1021/acsami.5b10697.
- ~~100-107.~~ X. Zhang, Z. Zhang, Z. Zhong, R. Zhuo, Amphiphilic Block-Graft Copolymers Poly(ethylene glycol)-b-(polycarbonates-g-palmitate) Prepared via the Combination of Ring-Opening Polymerization and Click Chemistry, *J. Polym. Sci. Part A Polym. Chem.* 50 (2012) 2687–2696. doi:10.1002/pola.26051.
- ~~101-108.~~ S. Haas, Y. Chen, C. Fuchs, S. Handschuh, M. Steuber, H. Schönherr, Amphiphilic Block Copolymer Vesicles for Active Wound Dressings: Synthesis of Model Systems and Studies of Encapsulation and Release, *Macromol. Symp.* 328 (2013) 73–79. doi:10.1002/masy.201350608.
- ~~102-109.~~ M. Boffito, P. Sirianni, A.M. Di Rienzo, V. Chiono, Thermosensitive block copolymer hydrogels based on poly( $\epsilon$ -caprolactone) and polyethylene glycol for biomedical applications: State of the art and future perspectives, *J. Biomed. Mater. Res. Part A.* 103 (2014) 1276–1290. doi:10.1002/jbm.a.35253.
- ~~103-110.~~ Z. Li, B.H. Tan, Towards the development of polycaprolactone based amphiphilic block copolymers: molecular design, self-assembly and biomedical

- applications, *Mater. Sci. Eng. C.* 45 (2014) 620–634. doi:10.1016/j.msec.2014.06.003.
- 404-111. J. Cappello, J. Crissman, M. Dorman, M. Mikolajczak, G. Textor, M. Marquet, F. Ferrari, Genetic engineering of structural protein polymers, *Biotechnol. Prog.* 6 (1990) 198–202. doi:10.1021/bp00003a006.
- 405-112. D.A. Tirrell, M.J. Fournier, T.L. Mason, Protein engineering for materials applications, *Curr. Opin. Struct. Biol.* 1 (1991) 638–641. doi:10.1016/s0959-440x(05)80089-2.
- 406-113. H. Li, N. Kong, B. Laver, J. Liu, Hydrogels Constructed from Engineered Proteins, *Small.* 12 (2016) 973–987. doi:10.1002/smll.201502429.
- 407-114. S. Cereceres, T. Touchet, M.B. Browning, C. Smith, J. Rivera, M. Höök, C. Whitfield-Cargile, B. Russell, E. Cosgriff-Hernandez, Chronic Wound Dressings Based on Collagen-Mimetic Proteins, *Adv. Wound Care.* 4 (2015) 444–456. doi:10.1089/wound.2014.0614.
- 408-115. J. Maitra, V.K. Shukla, Cross-linking in Hydrogels- A Review, *American J. Poly. Sci.* 4 (2014): 25-31. doi:10.5923/j.ajps.20140402.01.
- 409-116. C. Witthayaprapakorn, R. Molloy, Design and Preparation of Synthetic Hydrogels by Redox Initiation via Free Radical Polymerisation for Biomedical Use as Wound Dressings, *Adv. Mater. Res.* 506 (2012) 315–318. doi:10.4028/www.scientific.net/amr.506.315.
- 410-117. C. Witthayaprapakorn, Design and Preparation of Synthetic Hydrogels Via Photopolymerisation for Biomedical Use as Wound Dressings, *Procedia Eng.* 8 (2011) 286–291. doi:10.1016/j.proeng.2011.03.053.
- 411-118. H. Chen, X. Xing, H. Tan, Y. Jia, T. Zhou, Y. Chen, Z. Ling, X. Hu, Covalently antibacterial alginate-chitosan hydrogel dressing integrated gelatin microspheres containing tetracycline hydrochloride for wound healing, *Mater. Sci. Eng. C.* 70 (2017) 287–295. doi:10.1016/j.msec.2016.08.086.
- 412-119. B. Gupta, M. Tummalapalli, B.L. Deopura, M.S. Alam, Preparation and characterization of in-situ crosslinked pectin–gelatin hydrogels, *Carbohydr. Polym.* 106 (2014) 312–318. doi:10.1016/j.carbpol.2014.02.019.
- 413-120. M.F. Akhtar, M. Hanif, N.M. Ranjha, Methods of synthesis of hydrogels ... A review, *Saudi Pharm. J.* 24 (2016) 554–559. doi:10.1016/j.jsps.2015.03.022.
- 414-121. Z. Li, B.H. Tan, Towards the development of polycaprolactone based amphiphilic block copolymers: molecular design, self-assembly and biomedical applications, *Mater. Sci. Eng. C.* 45 (2014) 620–634. doi:10.1016/j.msec.2014.06.003.
- 415-122. B. Boonkaew, P.M. Barber, S. Rengpipat, P. Supaphol, M. Kempf, J. He, V.T. John, L. Cuttle, Development and Characterization of a Novel, Antimicrobial, Sterile Hydrogel Dressing for Burn Wounds: Single-Step Production with Gamma Irradiation Creates Silver Nanoparticles and Radical Polymerization, *J Pharm Sci.* 103 (2014): 3244-3253. doi:10.1002/jps.24095.
- 416-123. K.A. Juby, C. Dwivedi, M. Kumar, S. Kota, H.S. Misra, P.N. Bajaj, Silver nanoparticle-loaded PVA/gum acacia hydrogel: Synthesis,

characterization and antibacterial study, *Carbohydr. Polym.* 89 (2012) 906–913. doi:10.1016/j.carbpol.2012.04.033.

417-124. Y. Zhou, Y. Zhao, L. Wang, L. Xu, M. Zhai, S. Wei, Radiation synthesis and characterization of nanosilver/gelatin/carboxymethyl chitosan hydrogel, *Radiat. Phys. Chem.* 81 (2012) 553–560. doi:10.1016/j.radphyschem.2012.01.014.

125. Kharkar PM, Rehmann MS, Skeens KM, Maverakis E, Kloxin AM. Thiol-ene click hydrogels for therapeutic delivery. *ACS biomaterials science & engineering* 2016;2(2):165-179.

126. Xu K, Cantu DA, Fu Y, Kim J, Zheng X, Hematti P, Kao WJ. Thiol-ene Michael-type formation of gelatin/poly(ethylene glycol) biomatrices for three-dimensional mesenchymal stromal/stem cell administration to cutaneous wounds. *Acta Biomaterialia* 2013;9(11):8802-8814.

127. Goh M, Hwang Y, Tae G. Epidermal growth factor loaded heparin-based hydrogel sheet for skin wound healing. *Carbohydrate Polymers* 2016;147:251-260.

128. Gharibi R, Yeganeh H, Abdali Z. Preparation of antimicrobial wound dressings via thiol-ene photopolymerization reaction. *J Mater Sci* 2018;53(3):1581-1595.

418-129. A. Chhatri, J. Bajpai, A.K. Bajpai, S.S. Sandhu, N. Jain, J. Biswas, Cryogenic fabrication of savlon loaded macroporous blends of alginate and polyvinyl alcohol (PVA). Swelling, deswelling and antibacterial behaviors, *Carbohydr. Polym.* 83 (2011) 876–882. doi:10.1016/j.carbpol.2010.08.077.

419-130. R.N. Oliveira, G.B. McGuinness, M.E.T. Ramos, C.E. Kajiyama, R.M.S.M. Thiré, Properties of PVA Hydrogel Wound-Care Dressings Containing UK Propolis, *Macromol. Symp.* 368 (2016) 122–127. doi:10.1002/masy.201500149.

420-131. M.R. Hwang, J.O. Kim, J.H. Lee, Y.I. Kim, J.H. Kim, S.W. Chang, S.G. Jin, J.A. Kim, W.S. Lyoo, S.S. Han, S.K. Ku, C.S. Yong, H.G. Choi, Gentamicin-Loaded Wound Dressing With Polyvinyl Alcohol/Dextran Hydrogel: Gel Characterization and *In Vivo* Healing Evaluation. *AAPS PharmSciTech*, **11** (2010): 1092 – 1103. doi: 10.1208/s12249-010-9474-0.

421-132. S. Sakai, M. Tsumura, M. Inoue, Y. Koga, K. Fukano, M. Taya, Polyvinyl alcohol-based hydrogel dressing gellable on-wound via a co-

enzymatic reaction triggered by glucose in the wound exudate, *J. Mater. Chem. B.* 1 (2013) 5067-5075. doi:10.1039/c3tb20780c.

422-133. M. Wang, L. Xu, H. Hu, M. Zhai, J. Peng, Y. Nho, J. Li, G. Wei, Radiation synthesis of PVP/CMC hydrogels as wound dressing, *Nucl. Instruments Methods Phys. Res. Sect. B Beam Interact. with Mater. Atoms.* 265 (2007) 385–389. doi:10.1016/j.nimb.2007.09.009.

423-134. B. Singh, L. Pal, Radiation crosslinking polymerization of sterculia polysaccharide–PVA–PVP for making hydrogel wound dressings, *Int. J. Biol. Macromol.* 48 (2011) 501–510. doi:10.1016/j.ijbiomac.2011.01.013.

424-135. R. Singh, D. Singh, Radiation synthesis of PVP/alginate hydrogel containing nanosilver as wound dressing, *J. Mater. Sci. Mater. Med.* 23 (2012) 2649–2658. doi:10.1007/s10856-012-4730-3.

425-136. K. Plungpongpan, K. Koyanukkul, A. Kaewvilai, N. Nootsuwan, P. Kewsuwan, A. Laobuthee, Preparation of PVP/MHEC Blended Hydrogels via Gamma Irradiation and their Calcium ion Uptaking and Releasing Ability, *Energy Procedia.* 34 (2013) 775–781. doi:10.1016/j.egypro.2013.06.813.

426-137. D. Archana, B.K. Singh, J. Dutta, P.K. Dutta, In vivo evaluation of chitosan–PVP–titanium dioxide nanocomposite as wound dressing material, *Carbohydr. Polym.* 95 (2013) 530–539. doi:10.1016/j.carbpol.2013.03.034.

427-138. A.I. Raafat, M. Eid, M. El-Arnaouty, Radiation synthesis of superabsorbent CMC based hydrogels for agriculture applications, *Nucl. Instruments Methods Phys. Res. Sect. B Beam Interact Mater. Atoms.* 283 (2012) 71–76. doi:10.1016/j.nimb.2012.04.011.

428-139. G.J.M. Fachine, J.A.G. Barros, L.H. Catalani, Poly(N-vinyl-2-pyrrolidone) hydrogel production by ultraviolet radiation: new methodologies to accelerate crosslinking, *Polymer.* 45 (2004) 4705–4709. doi:10.1016/j.polymer.2004.05.006.

429-140. Ž. Jovanović, A. Krklješ, J. Stojkowska, S. Tomić, B. Obradović, V. Mišković-Stanković, Z. Kačarević-Popović, Synthesis and characterization of silver/poly(N-vinyl-2-pyrrolidone) hydrogel nanocomposite obtained by in situ radiolytic method, *Radiat. Phys. Chem.* 80 (2011) 1208–1215. doi:10.1016/j.radphyschem.2011.06.005.

430-141. T. Khampieng, S. Wongkittithavorn, S. Chairawut, P. Ekabutr, P. Pavasant, P. Supaphol, Silver nanoparticles-based hydrogel: Characterization of material parameters for pressure ulcer dressing applications, *J. Drug Deliv. Sci. Technol.* 44 (2018) 91–100. doi:10.1016/j.jddst.2017.12.005.

431-142. J. Koehler, L. Wallmeyer, S. Hedtrich, A.M. Goepferich, F.P. Brandl, pH-Modulating Poly(ethylene glycol)/Alginate Hydrogel Dressings for the Treatment of Chronic Wounds, *Macromol. Biosci.* 17 (2017) 1600369. doi:10.1002/mabi.201600369.

432-143. Q. Xu, S. A, Y. Gao, L. Guo, J. Creagh-Flynn, D. Zhou, U. Greiser, Y. Dong, F. Wang, H. Tai, W. Liu, W. Wang, W. Wang, A hybrid injectable hydrogel from hyperbranched PEG macromer as a stem cell delivery and

retention platform for diabetic wound healing, *Acta Biomater.* 75 (2018) 63–74. doi:10.1016/j.actbio.2018.05.039.

433-144. S. Koosehgo, M. Ebrahimian-Hosseiniabadi, M. Alizadeh, A. Zamanian, Preparation and characterization of in situ chitosan/polyethylene glycol fumarate/thymol hydrogel as an effective wound dressing, *Mater. Sci. Eng. C.* 79 (2017) 66–75. doi:10.1016/j.msec.2017.05.001.

434-145. K. Nalampang, R. Panjakha, R. Molloy, B.J. Tighe, Structural effects in photopolymerized sodium AMPS hydrogels crosslinked with poly(ethylene glycol) diacrylate for use as burn dressings, *J. Biomater. Sci. Polym. Ed.* 24 (2013) 1291–1304. doi:10.1080/09205063.2012.755601.

435-146. M. Goh, Y. Hwang, G. Tae, Epidermal growth factor loaded heparin-based hydrogel sheet for skin wound healing, *Carbohydr. Polym.* 147 (2016): 251-260. doi:10.1016/j.carbpol.2016.03.072.

436-147. S. Pacelli, P. Paolicelli, I. Dreesen, S. Kobayashi, A. Vitalone, M.A. Casadei, Injectable and photocross-linkable gels based on gellan gum methacrylate: A new tool for biomedical application, *Int. J. Biol. Macromol.* 72 (2015): 1335-1342. doi:10.1016/j.ijbiomac.2014.10.046.

437-148. Y. Dong, W.U. Hassan, R. Kennedy, U. Greiser, A. Pandit, Y. Garcia, W. Wang, Performance of an in situ formed bioactive hydrogel dressing from a PEG-based hyperbranched multifunctional copolymer, *Acta Biomaterialia.* 10 (2014): 2076-2085. doi:10.1016/j.actbio.2013.12.045.

438-149. S. Atzet, S. Curtin, P. Trinh, S. Bryant, B. Ratner, Degradable Poly(2-hydroxyethyl methacrylate)-co-polycaprolactone Hydrogels for Tissue Engineering Scaffolds, *Biomacromolecules.* 9 (2008): 3370-3377. doi:10.1021/bm800686h.

439-150. S.L. Tomić, M.M. Mičić, S.N. Dobić, J.M. Filipović, E.H. Suljovrujić, Smart poly(2-hydroxyethyl methacrylate/itaconic acid) hydrogels for biomedical application, *Radiat. Phys. Chem.* 79 (2010): 643-649. doi:10.1016/j.radphyschem.2009.11.015.

440-151. G.M. Halpenny, R.C. Steinhardt, K.A. Okialda, P.K. Mascharak, Characterization of pHEMA-based hydrogels that exhibit light-induced bactericidal effect via release of NO. *J. Mater. Sci. Mater. Med.* 20 (2009): 2353-2360. doi:10.1007/s10856-009-3795-0.

441-152. D. Philip, Honey mediated green synthesis of silver nanoparticles, *Spectrochimica Acta Part A: Molecular and Biomolecular Spectroscopy.* 75 (2010): 1078-1081. doi:10.1016/j.saa.2009.12.058.

442-153. C. He, L. Liu, Z. Fang, J. Li, J. Guo, J. Wei, Formation and characterization of silver nanoparticles in aqueous solution via ultrasonic irradiation, *Ultrason. Sonochem.* 21 (2014): 542-548. doi:10.1016/j.ultsonch.2013.09.003.

443-154. S. Raj, S.C. Mali, R. Trivedi, Green synthesis and characterization of silver nanoparticles using *Enicostemma axillare* (Lam.) leaf extract, *Biochem. Biophys. Res. Commun.* 2018. In Press. doi:10.1016/j.bbrc.2018.08.045.

- 444-155. I. Ghiuță, D. Cristea, C. Croitoru, J. Kost, R. Wenkert, I. Vyrides, A. Anayiotos, D. Munteanu, Characterization and antimicrobial activity of silver nanoparticles, biosynthesized using *Bacillus* species, *Appl. Surf. Sci.* 438 (2018): 66-73. doi:10.1016/j.apsusc.2017.09.163.
- 445-156. M.N. Siddiqui, H.H. Redhwi, I. Tsagkalias, C. Softas, M.D. Ioannidou, D.S. Achilias, Synthesis and characterization of poly(2-hydroxyethyl methacrylate)/silver hydrogel nanocomposites prepared via in situ radical polymerization, *Thermochimica Acta.* 643 (2016): 53-64. doi:10.1016/j.tca.2016.09.017.
- 446-157. Z. Di, Z. Shi, M.W. Ullah, S. Li, G. Yang, A transparent wound dressing based on bacterial cellulose whisker and poly(2-hydroxyethyl methacrylate). *Int. J. Biol. Macromol.* 105 (2017): 638-644. doi:10.1016/j.ijbiomac.2017.07.075.
- 447-158. M. Nistor, A.P. Chiriac, C. Vasile, L. Verestiuc, L.E. Nita, Synthesis of hydrogels based on poly(NIPAM) inserted into collagen sponge, *Colloids and Surfaces B: Biointerfaces.* 87 (2011): 382-390. doi:10.1016/j.colsurfb.2011.05.046.
- 448-159. J. Shepherd, P. Sarker, S. Rimmer, L. Swanson, S. MacNeil, I. Douglas, Hyperbranched poly(NIPAM) polymers modified with antibiotics for the reduction of bacterial burden in infected human tissue engineered skin, *Biomaterials.* 32 (2011): 258-267. doi:10.1016/j.biomaterials.2010.08.084.
- 449-160. K. Zubik, P. Singhsa, Y. Wang, H. Manuspiya, R. Narain, Thermo-Responsive Poly(N-Isopropylacrylamide)-Cellulose Nanocrystals Hybrid Hydrogels for Wound Dressing, *Polymers.* 9 (2017): 119. 9 (2017) 119. doi:10.3390/polym9040119.
- 450-161. B. Jiang, J.C. Larson, P.W. Drapala, V.H. Pérez-Luna, J. Kang-Mieler, E.M. Brey, Investigation of lysine acrylate containing poly(N-isopropylacrylamide) hydrogels as wound dressings in normal and infected wounds, *J. Biomedical Materials Research Part B: Applied Biomaterials.* 100B (2012): 668-676. doi:10.1002/jbm.b.31991.
- 451-162. S. Chen, J. Shi, M. Zhang, Y. Chen, X. Wang, L. Zhang, Z. Tian, Y. Yan, Q. Li, W. Zhong, M. Xing, L. Zhang, L. Zhang, Mesenchymal stem cell-laden anti-inflammatory hydrogel enhances diabetic wound healing, *Scientific Reports.* 5 (2015). doi:10.1038/srep18104.
- 452-163. Y. Wu, L. Chen, P.G. Scott, E.E. Tredge, Mesenchymal Stem Cells Enhance Wound Healing Through Differentiation and Angiogenesis, *Stem Cells.* 25 (2007): 2648-2659. doi:10.1634/stemcells.2007-0226.
- 453-164. D. Hoefler, J.K. Schnepf, T.R. Hammer, M. Fischer, C. Marquardt, Biotechnologically produced microbial alginate dressings show enhanced gel forming capacity compared to commercial alginate dressings of marine origin, *J. Mater. Sci. Mater. Med.* 26 (2015). doi:10.1007/s10856-015-5492-5.
- 454-165. I. Malagurski, S. Levic, M. Mitric, V. Pavlovic, S. Dimitrijevic-Brankovic, Bimetallic alginate nanocomposites: New antimicrobial biomaterials for

biomedical application, *Mater. Lett.* 212 (2018): 32-36. doi:10.1016/j.matlet.2017.10.046.

455-166. S. Kondaveeti, P.V. de Assis. Bueno, A.M.Carmona-Ribeiro, F. Esposito, N. Lincopan, M.R. Sierakowski, D.F.S. Petri, Microbicidal gentamicin-alginate hydrogels, *Carbohydr. Polym.* 186 (2018): 59-167. doi:10.1016/j.carbpol.2018.01.044.

456-167. O.Catanzano, V. D'Esposito, S. Acierno, M.R. Ambrosio, C. De Caro, C. Avagliano, P. Russo, R. Russo, A. Miro, F. Ungaro, A. Calignano, P. Formisano, F. Quaglia, Alginate-hyaluronan composite hydrogels accelerate wound healing process, *Carbohydr. Polym.* 131 (2015): 407-414. doi:10.1016/j.carbpol.2015.05.081.

457-168. T. Wu, J. Huang, Y. Jiang, Y. Hu, X. Ye, D. Liu, J. Chen, Formation of hydrogels based on chitosan/alginate for the delivery of lysozyme and their antibacterial activity, *Food Chem.* 240 (2018): 361-369. doi:10.1016/j.foodchem.2017.07.052.

458-169. J. Kurczewska, P. Pecyna, M. Ratajczak, M. Gajęcka, G. Schroeder, Halloysite nanotubes as carriers of vancomycin in alginate-based wound dressing, *Saudi Pharmaceutical Journal.* 25 (2017): 911-920. doi:10.1016/j.jsps.2017.02.007.

459-170. Y.H. Lee, J.J. Chang, M.C. Yang, C.T. Chien, W.F. Lai, Acceleration of wound healing in diabetic rats by layered hydrogel dressing, *Carbohydr. Polym.* 88 (2012): 809-819. doi:10.1016/j.carbpol.2011.12.045.

460-171. B. Balakrishnan, M. Mohanty, P. Umashankar, A. Jayakrishnan, Evaluation of an in situ forming hydrogel wound dressing based on oxidized alginate and gelatin, *Biomaterials.* 26 (2005): 6335-6342. doi:10.1016/j.biomaterials.2005.04.012.

461-172. A. Saari, T. Sedlacek, V. Kasparkova, T. Kitano, P. Saha, On the characterization of sodium alginate/gelatine-based hydrogels for wound dressing, *J. Appl. Polym. Sci.* 126 (2012): E79-88. doi:10.1002/app.36590.

462-173. R.M. Abdel-Rahman, R. Hrdina, A.M. Abdel-Mohsen, M.M.G. Fouda, A.Y. Soliman, F.K. Mohamed, K. Mohsin, T.D. Pinto, Chitin and chitosan from Brazilian Atlantic Coast: Isolation, characterization and antibacterial activity, *Int. J. Biol. Macromol.* 80 (2015): 107-120. doi:10.1016/j.ijbiomac.2015.06.027.

463-174. S. Kumari, S.H. K. Annamareddy, S. Abanti, P. K. Rath, Physicochemical properties and characterization of chitosan synthesized from fish scales, crab and shrimp shells, *Int. J. Biol. Macromol.* 104 (2017): 1697-1705. doi:10.1016/j.ijbiomac.2017.04.119.

464-175. W. Mozalewska, R. Czechowska-Biskup, A.K. Olejnik, R.A. Wach, P. Ulański, J.M. Rosiak, Chitosan-containing hydrogel wound dressings prepared by radiation technique, *Radiat. Phys. Chem.* 134 (2017): 1-7. doi:10.1016/j.radphyschem.2017.01.003.

465-176. S.S. Behera, U. Das, A. Kumar, A. Bissoyi, A.K. Singh, Chitosan/TiO<sub>2</sub> composite membrane improves proliferation and survival of L929 fibroblast

cells: Application in wound dressing and skin regeneration, *Int. J. Biol. Macromol.* 98 (2017): 329-340. doi:10.1016/j.ijbiomac.2017.02.017.

466-177. D. Archana, B.K. Singh, J. Dutta, P.K. Dutta, Chitosan-PVP-nano silver oxide wound dressing: In vitro and in vivo evaluation, *Int. J. Biol. Macromol.* 73 (2015): 49-57. doi:10.1016/j.ijbiomac.2014.10.055.

467-178. M.P. Ribeiro, A. Espiga, D. Silva, P. Baptista, J. Henriques, C. Ferreira, J.C. Silva, J.P. Borges, E. Pires, P. Chaves, I.J. Correia, Development of a new chitosan hydrogel for wound dressing, *Wound Repair and Regeneration.* 17 (2009): 817-824. doi:10.1111/j.1524-475x.2009.00538.x.

468-179. T. Wang, X.K. Zhu, X.T. Xue, D.Y. Wu, Hydrogel sheets of chitosan, honey and gelatin as burn wound dressings, *Carbohydr. Polym.* 88 (2012): 75-83. doi:10.1016/j.carbpol.2011.11.069.

469-180. K. Pal, A.K. Banthia, D.K. Majumdar, Starch based hydrogel with potential biomedical application as artificial skin, *African J. Biomedical Res.* 9 (2006): 23-29. doi:10.4314/ajbr.v9i1.48769.

470-181. E.A. Kamoun, N-succinyl chitosan-dialdehyde starch hybrid hydrogels for biomedical applications, *J. of Adv. Res.* 7 (2016): 69-77. doi:10.1016/j.jare.2015.02.002.

471-182. Z. Hadisi, J. Nourmohammadi, S.M. Nassiri, The antibacterial and anti-inflammatory investigation of Lawsonia Inermis -gelatin-starch nano-fibrous dressing in burn wound, *Int. J. Biol. Macromol.* 107 (2018): 2008-2019. doi:10.1016/j.ijbiomac.2017.10.061.

472-183. E.A. Bursali, S. Coskun, M. Kizil, M. Yurdakoc, Synthesis, characterization and in vitro antimicrobial activities of boron/starch/polyvinyl alcohol hydrogels, *Carbohydr. Polym.* 83 (2011): 1377-1383. doi:10.1016/j.carbpol.2010.09.056.

473-184. J. Timmons, M. Bertram, G. Pirie, K. Duguid, Aquaform<sup>®</sup> hydrogel- a new formulation for an improved wound care performance. *Wounds UK*, 4(2008): 69-73.

474-185. R.M. Brown Jr, Bacterial Cellulose, in: G.O. Phillips, J.F. Kennedy, P.A. Williams (Eds.), *Cellulose: Structural and Functional Aspects*, Ellis Horwood Ltd, Chichester, 1989, pp. 145-151.

475-186. M.M. Abeer, A.M.C.I. Mohd, C. Martin, A review of bacterial cellulose-based drug delivery systems: their biochemistry, current approaches and future prospects, *J. Pharm. Pharmacol.* 66 (2014):1047-1061. doi:10.1111/jphp.12234.

[187. Gupta, A., et al., 2017, Physicochemical characterisation of biosynthetic bacterial cellulose as a potential wound dressing material, Brit J Pharmacy,2: S37-38](#)

476-188. F.K. Andrade, J.P. Silva, M. Carvalho, E.M.S. Castanheira, R. Soares, M. Gama, Studies on the hemocompatibility of bacterial cellulose, *J. of*

Biomedical Materials Research: Part A. 98A (2011): 554-566. doi:10.1002/jbm.a.33148.

477-189. R.A.N. Pértile, S. Moreira, R.M. Gil da Costa, A. Correia, L. Guãrdao, F. Gartner, M. Vilanova, M. Gama, Bacterial Cellulose: Long-Term Biocompatibility Studies, *J. of Biomaterials Sci. Polymer Ed.* 23 (2012): 1339-1354. doi:10.1163/092050611x581516.

478-190. M. Pandey, N. Mohamad, W. Low, C. Martin, A.M.C.I. Mohd, Microwaved bacterial cellulose-based hydrogel microparticles for the healing of partial thickness burn wounds, *Drug Delivery and Translational Research.* 7 (2017): 89-99. doi:10.1007/s13346-016-0341-8.

479-191. O. Portal, W.A. Clark, D.J. Levinson, Microbial Cellulose Wound Dressing in the Treatment of Nonhealing Lower Extremity Ulcers, *Wounds.* 21(2009) 1-3.

480-192. T. Maneerung, S. Tokura, R. Rujiravanit, Impregnation of silver nanoparticles into bacterial cellulose for antimicrobial wound dressing, *Carbohydr. Polym.* 72 (2008): 43-51. doi:10.1016/j.carbpol.2007.07.025.

481-193. B. Wei, G. Yang, F. Hong, Preparation and evaluation of a kind of bacterial cellulose dry films with antibacterial properties, *Carbohydr. Polym.* 84 (2011): 533-538. doi:10.1016/j.carbpol.2010.12.017.

482-194. E. Trovatti, C.S.R. Freire, P.C. Pinto, I.F. Almeida, P. Costa, A.J.D. Silvestre, C.P. Neto, C. Rosado, Bacterial cellulose membranes applied in topical and transdermal delivery of lidocaine hydrochloride and ibuprofen: In vitro diffusion studies, *Int. J. Pharmce.* 435 (2012): 83-87. doi:10.1016/j.ijpharm.2012.01.002.

483-195. J. Wu, Y. Zheng, W. Song, J. Luan, X. Wen, Z. Wu, X. Chen, Q. Wang, S. Guo, In situ synthesis of silver-nanoparticles/bacterial cellulose composites for slow-released antimicrobial wound dressing, *Carbohydr. Polym.* 102 (2014): 762-771. doi:10.1016/j.carbpol.2013.10.093.

484-196. R. Reeves, A. Ribeiro, L. Lombardo, R. Boyer, J.B. Leach, Synthesis and Characterization of Carboxymethylcellulose-Methacrylate Hydrogel Cell Scaffolds, *Polymers.* 2 (2010): 252-264. doi:10.3390/polym2030252.

485-197. R. Rakhshaei, H. Namazi, A potential bioactive wound dressing based on carboxymethyl cellulose/ZnO impregnated MCM-41 nanocomposite hydrogel, *Materials Science and Engineering: C.* 73 (2017): 456-464. doi:10.1016/j.msec.2016.12.097.

486-198. H. Namazi, R. Rakhshaei, H. Hamishehkar, H.S. Kafil, Antibiotic loaded carboxymethylcellulose/MCM-41 nanocomposite hydrogel films as potential wound dressing, *Int. J. Biol. Macromol.* 85 (2016): 327-334. doi:10.1016/j.ijbiomac.2015.12.076.

487-199. R.N. Oliveira, A.P.D. Moreira, R.M. da Silva, M. Thiré, B. Quilty, T.M. Passos, P. Simon, M.C. Mancini, G.B. McGuinness, Absorbent polyvinyl alcohol-sodium carboxymethyl cellulose hydrogels for propolis delivery in wound healing applications, *Polymer Engineering & Science,* 2017: 1224-1233. doi:10.1002/pen.24500.

200. Omowumi Ogunleye, A., Bhat, A., Irorere, V.U., Hill, D., Williams, C. and Radecka, I. (2014) Poly-gamma-glutamic acid - Production, Properties and Applications. Microbiology . 161 (1) 1-17.

Formatted: Font color: Custom Color(RGB(83,86,90)), Pattern: Clear (White)

201. Khalil, IR., Irorere, VU., Radecka, I., Burns, ATH., Kowalczyk, M., Mason, JL., Khechara, M. (2017) Bacterial-Derived Polymer Poly-γ-Glutamic Acid (γ-PGA)-Based Micro/Nanoparticles as a Delivery System for Antimicrobials and Other Biomedical Applications. International Journal of Molecular Sciences , 2017, 18, 313; doi:10.3390/ijms18020313

202. Lu Shi, Ning Yang, Hao Zhang, Li Chen, Lei Tao, Yen Wei, Hui Liu, Ying Luo. A novel poly(γ-glutamic acid)/silk-sericin hydrogel for wound dressing: Synthesis, characterization and biological evaluation. <https://doi.org/10.1016/j.msec.2014.12.047>,

Formatted: Font color: Custom Color(RGB(83,86,90)), Pattern: Clear (White)

203. Zhang L, Ma Y, Pan X, Chen S, Zhuang H, Wang S. A composite hydrogel of chitosan/heparin/poly (γ-glutamic acid) loaded with superoxide dismutase for wound healing. Carbohydrate Polymers 2018;180:168-174.

Formatted: Font: (Default) Arial, 12 pt, Font color: Custom Color(RGB(83,86,90)), Pattern: Clear (White)

~~188-~~204. H. Xie, X. Chen, X. Shen, Y. He, W. Chen, Q. Luo, W. Ge, W. Yuan, X. Tang, D. Hou, D. Jiang, Q. Wang, Y. Liu, Q. Liu, K. Li, Preparation of chitosan-collagen-alginate composite dressing and its promoting effects on wound healing, Int. J. Biol. Macromol. 107 (2018): 93-104. doi:10.1016/j.ijbiomac.2017.08.142.

~~189-~~205. M. Michalska-Sionkowska, M. Walczak, A. Sionkowska, Antimicrobial activity of collagen material with thymol addition for potential application as wound dressing, Polym. Test. 63 (2017): 360-366. doi:10.1016/j.polymertesting.2017.08.036.

~~190-~~206. L.I.F.Moura, A.M.A. Dias, E. Suesca, S. Casadiegos, E.C. Leal, M.R. Fontanilla, L. Carvalho, H.C. de Sousa, E. Carvalho, Neurotensin-loaded collagen dressings reduce inflammation and improve wound healing in diabetic mice, Biochimica et Biophysica Acta (BBA) - Molecular Basis of Disease. 1842 (2014): 32-43. doi:10.1016/j.bbadis.2013.10.009.

~~191-~~207. A. Oryan, M. Jalili, A. Kamali, B. Nikahval, The concurrent use of probiotic microorganism and collagen hydrogel/scaffold enhances burn wound healing: An in vivo evaluation, Burns 2018. In Press, doi:10.1016/j.burns.2018.05.016.

- ~~192-208.~~ C.A. Fleck, R. Simman, Modern Collagen Wound Dressings: Function and Purpose, *The Journal of the American College of Certified Wound Specialists*. 2 (2010): 50-54. doi:10.1016/j.jcws.2010.12.003.
- ~~193-209.~~ Z. Zhou, J. Chen, C. Peng, T. Huang, H. Zhou, B. Ou, J. Chen, Q. Liu, S. He, D. Cao, H. Huang, L. Xiang, Fabrication and Physical Properties of Gelatin/Sodium Alginate/Hyaluronic Acid Composite Wound Dressing Hydrogel, *Journal of Macromolecular Science, Part A*. 51 (2014): 318-325. doi:10.1080/10601325.2014.882693.
- ~~194-210.~~ D.S. Yoon, Y. Lee, H.A. Ryu, Y. Jang, K.M. Lee, Y. Choi, W.J. Choi, M. Lee, K.M. Park, K.D. Park, J.W. Lee, Cell recruiting chemokine-loaded sprayable gelatin hydrogel dressings for diabetic wound healing, *Acta Biomaterialia*. 38 (2016): 59-68. doi:10.1016/j.actbio.2016.04.030.
- ~~195-211.~~ S. Kanokpanont, S. Damrongsakkul, J. Ratanavaraporn, P. Aramwit, An innovative bi-layered wound dressing made of silk and gelatin for accelerated wound healing, *Int. J. Pharmceut.* 436 (2012): 141-153. doi:10.1016/j.ijpharm.2012.06.046.
- ~~196-212.~~ J. Wang, J. Wei, Interpenetrating network hydrogels with high strength and transparency for potential use as external dressings, *Materials Science and Engineering: C*. 80 (2017): 460-467. doi:10.1016/j.msec.2017.06.018.
- ~~197-213.~~ R. Faturechi, A. Karimi, A. Hashemi, H. Yousefi, M. Navidbakhsh, Influence of Poly(acrylic acid) on the Mechanical Properties of Composite Hydrogels, *Adv. Polym. Technol.* 34 (2015): 21487. doi:10.1002/adv.21487.
- ~~198-214.~~ P. Luo, L. Liu, W. Xu, L. Fan, M. Nie, Preparation and characterization of aminated hyaluronic acid/oxidized hydroxyethyl cellulose hydrogel, *Carbohydr. Polym.* 199 (2018): 170-177. doi:10.1016/j.carbpol.2018.06.065.
- ~~199-215.~~ X. Xu, A.K. Jha, D.A. Harrington, M. Farach-Carson, X. Jia, Hyaluronic acid-based hydrogels: from a natural polysaccharide to complex networks, *Soft. Matter*. 8 (2012): 3280-3294. doi:10.1039/c2sm06463d.
- ~~200-216.~~ L.P. da Silva, T.C. Santos, D.B. Rodrigues, R.P. Pirraco, M.T. Cerqueira, R.L. Reis, V.M. Correlo, A.P. Marques, Stem Cell-Containing Hyaluronic Acid-Based Spongy Hydrogels for Integrated Diabetic Wound Healing, *J. Invest. Dermatol.* 137 (2017): 1541-1551. doi:10.1016/j.jid.2017.02.976.
- ~~201-217.~~ L. Zhao, H.J. Gwon, Y.M. Lim, Y.C. Nho, S.Y. Kim, Gamma ray-induced synthesis of hyaluronic acid/chondroitin sulfate-based hydrogels for biomedical applications, *Radiat. Phys. Chem.* 106 (2015): 404-412. doi:10.1016/j.radphyschem.2014.08.018.
- ~~202-218.~~ A.R. Unnithan, N.A.M. Barakat, P.B. Tirupathi Pichiah, G. Gnanasekaran, R. Nirmala, Y.S. Cha, C.H. Jung, M. El-Newehy, H.Y. Kim, Wound-dressing materials with antibacterial activity from electrospun polyurethane-dextran nanofiber mats containing ciprofloxacin HCl, *Carbohydr. Polym.* 90 (2012): 1786-1793. doi:10.1016/j.carbpol.2012.07.071.
- ~~203-219.~~ K. Szafulera, R.A. Wach, A.K. Olejnik, J.M. Rosiak, P. Ulański, Radiation synthesis of biocompatible hydrogels of dextran methacrylate,

Radiat. Phys. Chem. 142 (2018): 115-120.  
doi:10.1016/j.radphyschem.2017.01.004.

~~204-220.~~ M. Alibolandi, M. Mohammadi, S.M. Taghdisi, K. Abnous, M. Ramezani, Synthesis and preparation of biodegradable hybrid dextran hydrogel incorporated with biodegradable curcumin nanomicelles for full thickness wound healing, *Int. J. Pharm.* 532 (2017): 466-477. doi:10.1016/j.ijpharm.2017.09.042.

~~205-221.~~ G. Sun, X. Zhang, Y.I. Shen, R. Sebastian, L.E. Dickinson, K. Fox-Talbot, M. Reinblatt, C. Steenbergen, J.W. Harmon, S. Gerecht, Dextran hydrogel scaffolds enhance angiogenic responses and promote complete skin regeneration during burn wound healing, *Proceedings of the National Academy of Sciences.* 108 (2011): 20976-20981. doi:10.1073/pnas.1115973108.

~~206-222.~~ Y. Hu, M.G. Gänzle, Effect of temperature on production of oligosaccharides and dextran by *Weissella cibaria* 10 M, *Int. J. Food Microbiol.* 280 (2018): 27-34. doi:10.1016/j.ijfoodmicro.2018.05.003.

~~207-223.~~ J. Grip, R.E. Engstad, I. Skjæveland, N. Škalko-Basnet, J. Isaksson, P. Basnet, A.M. Holsæter, Beta-glucan-loaded nanofiber dressing improves wound healing in diabetic mice, *European Journal of Pharmaceutical Sciences.* 121 (2018): 269-280. doi:10.1016/j.ejps.2018.05.031.

~~208-224.~~ M. Salgado, S. Rodríguez-Rojo, R.L. Reis, M.J. Cocero, A.R.C. Duarte, Preparation of barley and yeast  $\beta$ -glucan scaffolds by hydrogel foaming: Evaluation of dexamethasone release, *The Journal of Supercritical Fluids.* 127 (2017): 158-165. doi:10.1016/j.supflu.2017.04.006.

~~209-225.~~ B. King, S. Barrett, K.F. Cutting, Clinical evaluation of a bioactive beta-glucan gel in the treatment of 'hard-to-heal' wounds, *J. Wound Care.* 26 (2017): 58-63. doi:10.12968/jowc.2017.26.2.58.

~~210-226.~~ J.S. Park, Y.M. Lim, J. Baik, J.O. Jeong, S.J. An, S.I. Jeong, H.J. Gwon, M.S. Khil, Preparation and evaluation of  $\beta$ -glucan hydrogel prepared by the radiation technique for drug carrier applications, *Int. J. Biol. Macromol.* 118 (2018): 333-339. doi:10.1016/j.ijbiomac.2018.06.068.

~~211-227.~~ V.K. Singh, I. Banerjee, T. Agarwal, K. Pramanik, M.K. Bhattacharya, K. Pal, Guar gum and sesame oil based novel bigels for controlled drug delivery, *Colloids and Surfaces B: Biointerfaces* 123 (2014): 582-592. doi:10.1016/j.colsurfb.2014.09.056.

~~212-228.~~ S. Thakur, G.S. Chauhan, J.H. Ahn, Synthesis of acryloyl guar gum and its hydrogel materials for use in the slow release of L-DOPA and L-tyrosine, *Carbohydr Polym.* 76 (2009): 513-520. doi:10.1016/j.carbpol.2008.11.012.

~~213-229.~~ H. Kono, F. Otaka, M. Ozaki, Preparation and characterization of guar gum hydrogels as carrier materials for controlled protein drug delivery, *Carbohydr Polym.* 111 (2014): 830-840. doi:10.1016/j.carbpol.2014.05.050.

~~214-230.~~ R. Ghadi, A. Jain, W. Khan, A.J. Domb, Microparticulate polymers and hydrogels for wound healing, *Wound Healing Biomaterials.* 2 (2016): 203-225. doi:10.1016/b978-1-78242-456-7.00010-6.

- ~~215-231.~~ P. Zoellner, H. Kapp, H. Smola, Clinical performance of a hydrogel dressing in chronic wounds: a prospective observational study, *J Wound Care*. 16 (2007):133-136. doi:10.12968/jowc.2007.16.3.27019.
- ~~216-232.~~ K. Bankoti, A.P. Rameshbabu, S. Datta, P.P. Maity, P. Goswami, P. Datta, S.K. Ghosh, A. Mitra, S. Dhara, Accelerated healing of full thickness dermal wounds by macroporous waterborne polyurethane-chitosan hydrogel scaffolds, *Materials Sci and Engineering: C*. 81 (2017):133-143. doi:10.1016/j.msec.2017.07.018.
- ~~217-233.~~ Q.A. Ijaz, N. Abbas, M.S. Arshad, A. Hussain, Shahiq-uz-Zaman, Z. Javaid, Synthesis and evaluation of pH dependent polyethylene glycol-co-acrylic acid hydrogels for controlled release of venlafaxine HCl, *J. Drug Del. Sci. and Tech*. 43 (2018): 221-232. doi:10.1016/j.jddst.2017.10.010.
- ~~218-234.~~ M. Champeau, V. Póvoa, L. Militão, F.M. Cabrini, G.F. Picheth, F. Meneau, C.P. Jara, E.P. de Araujo, M.G. de Oliveira, Supramolecular poly(acrylic acid)/F127 hydrogel with hydration-controlled nitric oxide release for enhancing wound healing, *Acta Biomaterialia*. 74 (2018): 312-325. doi:10.1016/j.actbio.2018.05.025.
- ~~219-235.~~ R. Jankaew, N. Rodkate, S. Lamlerthon, B. Rutnakornpituk, U. Wichai, G. Ross, M. Rutnakornpituk, "Smart" carboxymethylchitosan hydrogels crosslinked with poly(N-isopropylacrylamide) and poly(acrylic acid) for controlled drug release, *Polym Test*. 42 (2015): 26-36. doi:10.1016/j.polymertesting.2014.12.010.
- ~~220-236.~~ A. Nestic, V. Panic, S. Ostojic, D. Micic, I. Pajic-Lijakovic, A. Onjia, S. Velickovic, Physical-chemical behavior of novel copolymers composed of methacrylic acid and 2-acrylamido-2-methylpropane sulfonic acid, *Mater Chem Phys*. 174 (2016):156-163. doi:10.1016/j.matchemphys.2016.02.063.
- ~~221-237.~~ A.S. Hicyilmaz, A.K. Seckin, I. Cerkez, Synthesis, characterization and chlorination of 2-acrylamido-2-methylpropane sulfonic acid sodium salt-based antibacterial hydrogels. *React Funct. Polym*. 115 (2017):109-116. doi:10.1016/j.reactfunctpolym.2017.04.014.
- ~~222-238.~~ B. Boonkaew, M. Kempf, R. Kimble, P. Supaphol, L. Cuttle, Antimicrobial efficacy of a novel silver hydrogel dressing compared to two common silver burn wound dressings: Acticoat™ and PolyMem Silver®, *Burns*. 40 (2014): 89-96. doi:10.1016/j.burns.2013.05.011.